

# Photocatalytic disinfection using titanium dioxide: spectrum and mechanism of antimicrobial activity

Howard A. Foster · Iram B. Ditta · Sajnu Varghese · Alex Steele

Received: 11 February 2011 / Accepted: 12 February 2011 / Published online: 27 April 2011  
© Springer-Verlag 2011

**Abstract** The photocatalytic properties of titanium dioxide are well known and have many applications including the removal of organic contaminants and production of self-cleaning glass. There is an increasing interest in the application of the photocatalytic properties of TiO<sub>2</sub> for disinfection of surfaces, air and water. Reviews of the applications of photocatalysis in disinfection (Gamage and Zhang 2010; Chong et al., *Wat Res* 44 (10):2997–3027, 2010) and of modelling of TiO<sub>2</sub> action have recently been published (Dalrymple et al., *Appl Catal B* 98(1–2):27–38, 2010). In this review, we give an overview of the effects of photoactivated TiO<sub>2</sub> on microorganisms. The activity has been shown to be capable of killing a wide range of Gram-negative and Gram-positive bacteria, filamentous and unicellular fungi, algae, protozoa, mammalian viruses and bacteriophage. Resting stages, particularly bacterial endospores, fungal spores and protozoan cysts, are generally more resistant than the vegetative forms, possibly due to the increased cell wall thickness. The killing mechanism involves degradation of the cell wall and cytoplasmic membrane due to the production of reactive oxygen species such as hydroxyl radicals and hydrogen peroxide. This initially leads to leakage of cellular contents then cell lysis and may be followed by complete mineralisation of the organism. Killing is most efficient when there is close contact between the organisms and the TiO<sub>2</sub> catalyst. The killing

activity is enhanced by the presence of other antimicrobial agents such as Cu and Ag.

**Keywords** Antimicrobial · Disinfection · Mechanism · Photocatalysis · ROS · TiO<sub>2</sub> · Titania

## Introduction

The ability of titanium dioxide (titania, TiO<sub>2</sub>) to act as a photocatalyst has been known for 90 years (Renz 1921), and its role in the “chalking” of paint (formation of powder on the surface) is well known (Jacobsen 1949). Interest in the application of the photocatalytic properties of TiO<sub>2</sub> was revived when the photoelectrolysis of water was reported by Fujishima and Honda (1972), and this activity was soon exploited both for the ability to catalyse the oxidation of pollutants (Carey et al. 1976; Frank and Bard 1977) and the ability to kill microorganisms (Matusunga 1985; Matsunaga et al. 1985). Photocatalytic surfaces can be superhydrophilic, which means that water spreads on the surface, allowing dirt to be washed off, and commercial uses include self-cleaning windows (e.g. San Gobain Bioclean™, Pilkington Active™ and SunClean™; Chen and Poon 2009) and self-cleaning glass covers for highway tunnel lamps (Honda et al. 1998). There are currently over 11,000 publications on photocatalysis. Although an early study showed no improved antimicrobial activity of TiO<sub>2</sub> for disinfection of primary wastewater effluent (Carey and Oliver 1980), many subsequent studies have shown the usefulness of photocatalysis on TiO<sub>2</sub> for disinfection of water (Chong et al. 2010). These include killing of bacteria (Rincón and Pulgarin 2004a) and viruses from water supplies (Sjogren and Sierka 1994),

H. A. Foster (✉) · I. B. Ditta · S. Varghese · A. Steele  
Centre for Parasitology and Disease Research,  
School of Environment and Life Sciences,  
University of Salford, The Crescent,  
Salford, Greater Manchester M5 4WT, UK  
e-mail: h.a.foster@salford.ac.uk

tertiary treatment of wastewater (Araña et al. 2002), purifying drinking water (Wei et al. 1994; Makowski and Wardas 2001), treatment of wash waters from vegetable preparation (Selma et al. 2008) and in bioreactor design to prevent biofilm formation (Shiraishi et al. 1999). TiO<sub>2</sub>-coated filters have been used for the disinfection of air (Jacoby et al. 1998; Goswami et al. 1997, 1999; Lin and Li 2003a, b; Chan et al. 2005). The advantage of using photocatalysis along with conventional air filtration is that the filters are also self-cleaning. TiO<sub>2</sub> has also been used on a variety of other materials and applications (Table 1). The potential for killing cancer cells has also been evaluated (reviewed by Blake et al. 1999; Fujishima et al. 2000).

In recent years, there has been an almost exponential increase in the number of publications referring to photocatalytic disinfection (PCD), and the total number of publications now exceeds 800 (Fig. 1). Some of the early work was reviewed by Blake et al. (1999) and sections on photocatalytic disinfection have been included in several reviews (Mills and Le Hunte 1997; Fujishima et al. 2000, 2008; Carp et al. 2004); reviews of the use in disinfection of water (McCullagh et al. 2007; Chong et al. 2010) and modelling of TiO<sub>2</sub> action have been published (Dalrymple et al. 2010). In this


review, we explore the effects of photoactivated TiO<sub>2</sub> on microorganisms.

### Photocatalytic mechanism

For a more detailed discussion of the photochemistry, the reader is directed to the excellent reviews by Mills and Le Hunte (1997) and Hashimoto et al. (2005). TiO<sub>2</sub> is a semiconductor. The adsorption of a photon with sufficient energy by TiO<sub>2</sub> promotes electrons from the valence band ( $e_{vb}^-$ ) to the conduction band ( $e_{cb}^-$ ), leaving a positively charged hole in the valence band ( $h_{vb}^+$ ; Eq. 1). The band gap energy (energy required to promote an electron) of anatase is approx. 3.2 eV, which effectively means that photocatalysis can be activated by photons with a wavelength of below approximately 385 nm (i.e. UVA). The electrons are then free to migrate within the conduction band. The holes may be filled by migration of an electron from an adjacent molecule, leaving that with a hole, and the process may be repeated. The electrons are then free to migrate within the conduction band and the holes may be filled by an electron from an adjacent molecule. This process can be repeated. Thus, holes are also mobile. Electrons and holes may recombine (bulk recombination) a




**Table 1** Some antimicrobial applications of TiO<sub>2</sub>

Uses and applications	Publication
Building materials, e.g. concrete	Guo et al. (2009) Chen and Poon (2009)
Catheters to prevent urinary tract infections	Ohko et al. (2001) Yao et al. (2008c)
Coatings for bioactive surfaces	Ueda et al. (2010)
Dental implants	Suketa et al. (2005) Mo et al. (2007)
Fabrics	Gupta et al. (2008), Kangwansupamonkon et al. (2009), Wu et al. (2009a, b), Yuranova et al. (2006)
Food packaging films	Chawengkijwanich and Hayata (2008)
Lancets	Nakamura et al. (2007)
Metal pins used for skeletal traction	Tsuang et al. (2008)
Orthodontic wires	Chun et al. (2007)
Paint	Allen et al. (2008)
Photocatalytic tiles for operating theatres	Fujishima et al. (1997)
Plastics	Paschoalino and Jardim (2008) Cerrada et al. (2008) Fujishima et al. (1997)
Protection of marble from microbial corrosion	Poulios et al. (1999)
Surgical face masks	Li et al. (2006)
Tent materials	Nimitrakoolchai and Supothina (2008)
TiO <sub>2</sub> -coated wood	Chen et al. (2009)
TiO <sub>2</sub> -containing paper	Geng et al. (2008)

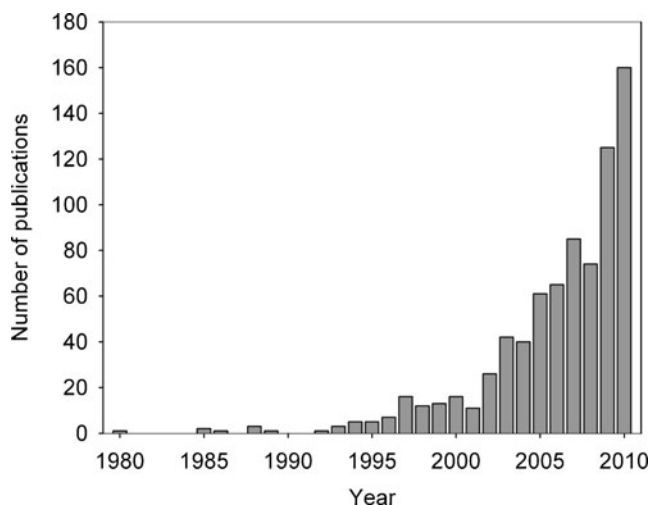

**Fig. 1** Number of publications on photocatalytic disinfection

non-productive reaction, or, when they reach the surface, react to give reactive oxygen species (ROS) such as  $O_2^{\cdot-}$  (2) and  $\cdot OH$  (3). These in solution can react to give  $H_2O_2$  (4), further hydroxyl (5) and hydroperoxyl (6) radicals. Reaction of the radicals with organic compounds results in mineralisation (7). Bulk recombination reduces the efficiency of the process, and indeed some workers have applied an electric field to enhance charge separation, properly termed photoelectrocatalysis (Harper et al. 2000).



There are three main polymorphs of  $TiO_2$ : anatase, rutile and brookite. The majority of studies show that anatase was the most effective photocatalyst and that rutile was less active; the differences are probably due to differences in the extent of recombination of electron and hole between the two forms (Miyagi et al. 2004). However, studies have shown that mixtures of anatase and rutile were more

effective photocatalysts than 100% anatase (Miyagi et al. 2004) and were more efficient for killing coliphage MS2 (Sato and Taya 2006a). One active commercially available preparations of  $TiO_2$  is Degussa P25 (Degussa Ltd., Germany) which contains approx. 80% anatase and 20% rutile. The increased activity is generally ascribed to interactions between the two forms, reducing bulk recombination. Brookite has been relatively little studied, but a recent paper showed that a brookite–anatase mixture was more active than anatase alone (Shah et al. 2008). A silver-doped multiphase catalyst was shown to have increased photocatalytic activity, but its antimicrobial activity was not reported (Yu et al. 2005a). Indoor use of photocatalytic disinfection is limited by the requirement for UVA irradiation. Modified catalysts can reduce the band gap so that visible light activates the photocatalysis. This has been shown for  $TiO_2$  combined with C, N and S, metals such as Sn, Pd, and Cu, and dyes (Fujishima and Zhang 2006), but activity is generally lower than when activated with UVA. This area is currently the subject of much research.

The antimicrobial activity of UVA-activated  $TiO_2$  was first demonstrated by Matsunaga and coworkers (Matsunaga 1985; Matsunaga et al. 1985). Since then, there have been reports on the use of photocatalysis for the destruction of bacteria, fungi, algae, protozoa and viruses as well as microbial toxins.  $TiO_2$  can be used in suspension in liquids or immobilised on surfaces (Kikuchi et al. 1997; Sunada et al. 1998; Kühn et al. 2003; Yu et al. 2003a; Brook et al. 2007; Yates et al. 2008a, b; Ditta et al. 2008). The ability to eliminate microorganisms on photocatalytic self-cleaning/self-disinfecting surfaces may provide a useful additional mechanism in the control of transmission of diseases along with conventional disinfection methods. Copper and silver ions are well characterised for their antimicrobial activities and can also enhance the photocatalytic activity. Combinations of  $Cu^{2+}$  and  $Ag^+$  with  $TiO_2$  therefore provide dual function surfaces (see below).

### Photocatalytic action on microorganisms

Photocatalysis has been shown to be capable of killing a wide range of organisms including Gram-negative and Gram-positive bacteria, including endospores, fungi, algae, protozoa and viruses, and has also been shown to be capable of inactivating prions (Paspaltsis et al. 2006). Photocatalysis has also been shown to destroy microbial toxins. As far as the authors are aware, only *Acanthamoeba* cysts and *Trichoderma asperellum* conidiospores have been reported to be resistant (see below), but these have not been extensively studied. The ability to kill all other groups of microorganisms suggests that the surfaces have the potential to be self-sterilising, particularly when combined

with Cu or Ag. However, for the present, it is correct to refer to photocatalytic surfaces or suspensions as being self-disinfecting rather than self-sterilising. Many studies have used pure cultures, although there are reports of photocatalytic activity against mixed cultures (van Grieken et al. 2010) and of natural communities (Armon et al. 1998; Araña et al. 2002; Cho et al. 2007a).

#### Gram-negative bacteria

The great majority of studies have been performed with *Escherichia coli*, and there are far too many to give a complete list in this review. Some examples of different strains used and applications are shown in Table 2. Examples of other Gram-negative bacteria that are susceptible to PCD are shown in Table 3. They include cocci, straight and curved rods, and filamentous forms from 19 different genera.

#### Gram-positive bacteria

Most studies showed that Gram-positive bacteria were more resistant to photocatalytic disinfection than Gram-negative bacteria (Kim et al. 2003; Liu and Yang 2003; Erkan et al. 2006; Pal et al. 2005, 2007; Muszkat et al. 2005; Hu et al. 2007; Sheel et al. 2008; Skorb et al. 2008). The difference is usually ascribed to the difference in cell wall structure between Gram-positive and Gram-negative bacteria. Gram-negative bacteria have a triple-layer cell wall with an inner membrane (IM), a thin peptidoglycan layer (PG) and an outer membrane (OM), whereas Gram-positive bacteria have a thicker PG and no OM. However, a few studies show that Gram-positive bacteria were more sensitive. *Lactobacillus* was more sensitive than *E. coli* on a Pt-doped TiO<sub>2</sub> catalyst (Matsunaga et al. 1985). methicillin-resistant *Staphylococcus aureus* (MRSA) and *E. coli* were more resistant than *Micrococcus luteus* (Kangwansupamonkon et al. 2009). Dunlop et al. (2010) showed that MRSA were more sensitive than an extended spectrum  $\beta$ -lactamase (ESBL)-producing *E. coli* strain, but less sensitive than *E. coli* K12. *Enterococcus faecalis* was more resistant than *E. coli*, but more sensitive than *Pseudomonas aeruginosa* (Luo et al. 2008). Conversely, Kubacka et al. (2008a) showed no difference in sensitivity between clinical isolates of *P. aeruginosa* and *E. faecalis*. Van Grieken et al. (2010) saw no difference in disinfection time for *E. coli* and *E. faecalis* in natural waters, but *E. faecalis* was more resistant in distilled water. These differences may relate to different affinities for TiO<sub>2</sub> (close contact between the cells and the TiO<sub>2</sub> is required for optimal activity—see below) as well as cell wall structure.

Gram-positive bacteria that have been shown to be killed by PCD are shown in Table 4 and include species of 17

different genera, including aerobic and anaerobic endospore formers. The endospores were uniformly more resistant than the vegetative cells to PCD.

#### Fungi, algae and protozoa

Fungi, algae and protozoa that have been shown to be susceptible to PCD are shown in Tables 5 and 6. These include 11 genera of filamentous fungi, 3 yeasts, 2 amoebae, 1 Apicomplexan, 1 diplomonad, 1 ciliate and 7 algae, including 1 diatom. Fungal spores were generally more resistant than vegetative forms, and *Trichoderma harzianum* spores in particular were resistant to killing under the conditions tested (Giannantonio et al. 2009). Cysts of *Acanthamoeba* showed only a 50% reduction during the treatment time and may have been killed if the treatment time had been extended (Sökmen et al. 2008).

#### Viruses

Viruses that have been shown to be killed by PCD are shown in Table 7.

Most studies were on *E. coli* bacteriophages in suspension, which have been demonstrated for icosahedral ssRNA viruses (MS2 and Q $\beta$ ), filamentous ssRNA virus (fr), ssDNA (phi-X174) and dsDNA viruses ( $\lambda$  and T4). Other bacteriophages include *Salmonella typhimurium* phage PRD-1, *Lactobacillus* phage PL1 and an unspecified *Bacteroides fragilis* phage. Mammalian viruses include poliovirus 1, avian and human influenza viruses, and SARS coronavirus (Table 7).

#### Bacterial toxins

Photocatalytic activity has been shown to be capable of inactivating bacterial toxins including Gram-negative endotoxin and algal and cyanobacterial toxins (Table 8).

#### Mechanism of killing of bacteria

The mode of action of photoactivated TiO<sub>2</sub> against bacteria has been studied with both Gram-positive and Gram-negative bacteria. The killing action was originally proposed to be via depletion of coenzyme A by dimerization and subsequent inhibition of respiration (Matsunaga et al. 1985, 1988). However, there is overwhelming evidence that the lethal action is due to membrane and cell wall damage. These studies include microscopy, detection of lipid peroxidation products, leakage of intercellular components, e.g. cations, RNA and protein, permeability to low-molecular-weight labels, e.g. *o*-nitrophenyl-galactoside (ONPG), and spectroscopic studies.

**Table 2** Examples of *E. coli* strains shown to be killed by photocatalytic disinfection on TiO<sub>2</sub>

Organism	Notes	Reference
<i>Escherichia coli</i>	WO <sub>3</sub> nanoparticle doped TiO <sub>2</sub>	Tatsuma et al. (2003)
<i>Escherichia coli</i>	Degussa P25 impregnated cloth filter	Vohra et al. (2006)
<i>Escherichia coli</i> ATCC 8739	Degussa P25 suspension	Cho et al. (2005)
<i>Escherichia coli</i> ATCC 11229	Degussa P25 coated plexiglass	Kühn et al. (2003)
<i>Escherichia coli</i> ATCC 13706	Degussa P25 immobilised on glass substrate	Rodriguez et al. (2007)
<i>Escherichia coli</i> ATCC 10536	Ag and CuO – TiO <sub>2</sub> hybrid catalysts	Brook et al. (2007), Ditta et al. (2008)
<i>Escherichia coli</i> ATCC 15153	Degussa P25 suspension	Ibáñez et al. (2003)
<i>Escherichia coli</i> ATCC 23505	Rfc sputter was used to deposit films of 120 nm thickness onto glass and steel substrates	Shieh et al. (2006)
<i>Escherichia coli</i> ATCC 23631	Degussa P25 applied to a plastic support	Sichel et al. (2007a)
<i>Escherichia coli</i> ATCC 25922	Aldrich TiO <sub>2</sub> 99.9% pure anatase	Sökmen et al. (2001)
<i>Escherichia coli</i> ATCC 25922	Aerosol deposited nanocrystalline film	Ryu et al. (2008)
<i>Escherichia coli</i> ATCC 27325	Degussa P25, suspension	Huang et al. (2000) Maness et al. (1999)
<i>Escherichia coli</i> ATCC-39713	Aerosil P25 suspension	Matsunaga et al. (1995)
<i>Escherichia coli</i> CAH57 (ESBL)	Thin film TiO <sub>2</sub>	Dunlop et al. (2010)
<i>Escherichia coli</i> CCRC 10675	TiO <sub>2</sub> and ZnO suspension	Liu and Yang (2003)
<i>Escherichia coli</i> CECT 101	Sol–gel microemulsion with an Ag overlayer	Kubacka et al. (2008b)
<i>Escherichia coli</i> DH 4α	Degussa P25 suspension	Lan et al. (2007)
<i>Escherichia coli</i> DH5α	Flow through reactor Anatase thin film on glass	Belhácová et al. (1999) Yu et al. (2002, 2003b)
<i>Escherichia coli</i> HB101	Degussa P25 suspension	Bekbölet and Araz (1996), Bekbölet (1997)
<i>Escherichia coli</i> HB101	Degussa P25 and Ag/P25 mixed suspension	Coleman et al. (2005)
<i>Escherichia coli</i> IFO 3301	Silica coated lime glass plates dip coated with TiO <sub>2</sub>	Kikuchi et al. (1997) Sunada et al. (2003b)
<i>Escherichia coli</i> IM303	TiO <sub>2</sub> coated air filter	Sato et al. (2003)
<i>Escherichia coli</i> JM109	Anatase thin film on glass	Yu et al. (2002)
<i>Escherichia coli</i> K12 ATCC10798	Degussa P25 suspension	Duffy et al. (2004) McLoughlin et al. (2004a, b) Pal et al. (2007)
<i>Escherichia coli</i> K12 ATCC10798	Degussa P25 coated glass fibre air filter	Pal et al. (2008)
<i>Escherichia coli</i> K12 (ATCC 23716)	Degussa P25	Rincon and Pulgarin (2003, 2004a)
<i>Escherichia coli</i> K12 (ATCC 2363)	Degussa P25 suspension	Marugan et al. (2008)
<i>Escherichia coli</i> K12	Degussa P25 suspension	Fernandez et al. (2005) Gumy et al. (2006a, b) Quisenberry et al. (2009)
<i>Escherichia coli</i> K12	Thin film TiO <sub>2</sub>	Dunlop et al. (2002)
<i>Escherichia coli</i> MG1655	Degussa P25 suspension	Gogniat and Dukan (2007)
<i>Escherichia coli</i> MM294	Degussa P25 suspension	Kim et al. (2004)
<i>Escherichia coli</i> NCIMB-4481	Immobilised TiO <sub>2</sub>	Butterfield et al. (1997)
<i>Escherichia coli</i> PHL1273	Degussa P25 suspension	Benabbou et al. (2007)
<i>Escherichia coli</i> PHL1273	Degussa P25 and millennium PC500	Guillard et al. (2008)
<i>Escherichia coli</i> S1400/95	Degussa P25 suspension	Robertson et al. (2005)
<i>Escherichia coli</i> 078	Thin films on glass substrate	Choi et al. (2004)
<i>Escherichia coli</i> XL1 Blue MRF	Anatase thin film on glass	Yu et al. (2002)

**Table 3** Other Gram-negative bacteria shown to be killed by photocatalytic disinfection

Organism	Notes	Reference
<i>Acinetobacter</i>	TiO <sub>2</sub> suspension	Kashyout et al. (2006)
<i>Acinetobacter baumannii</i>	C doped TiO <sub>2</sub>	Cheng et al. (2009)
<i>Aeromonas hydrophila</i> AWWX1	TiO <sub>2</sub> pellets	Kerstens et al. (1998)
<i>Anabaena</i>	TiO <sub>2</sub> -coated glass beads	Kim and Lee (2005)
<i>Bacteroides fragilis</i>	TiO <sub>2</sub> on orthopaedic implants	Tsuang et al. (2008)
Coliforms	Degussa P25 suspension	Araña et al. (2002)
Coliforms	Anatase suspension	Watts et al. (1995)
<i>Edwardsiella tarda</i>	Sol/gel-coated glass slides	Cheng et al. (2008)
<i>Enterobacter aerogenes</i>	Degussa P25 suspension	Ibáñez et al. (2003)
<i>Enterobacter cloacae</i> SM1	Anatase, spin-coated glass plates	Yao et al. (2007a)
<i>Erwinia carotovora</i> subsp. <i>carotovora</i>	Degussa P25 suspension	Muszkat et al. (2005)
<i>Erwinia carotovora</i> subsp. <i>carotovora</i> ZL1, subsp. <i>Carotovora</i> 3, subsp. <i>Carotovora</i> 7	Anatase, spin-coated glass lates	Yao et al. (2007a, b, 2008a, b)
Faecal coliforms	Anatase suspension	Watts et al. (1995)
<i>Flavobacterium</i> sp.	TiO <sub>2</sub> suspension and coated glass beads	Cohen-Yaniv et al. (2008)
<i>Fusobacterium nucleatum</i>	Thin film of anatase on titanium	Suketa et al. (2005), Bai et al. (2007)
<i>Legionella pneumophila</i> ATCC 33153	Degussa P25 suspension	Cheng et al. (2007)
<i>Legionella pneumophila</i> CCRC 16084	TiO <sub>2</sub> air filter + UVC	Li et al. (2003)
<i>Legionella pneumophila</i> GIFU-9888	Ultrasonic activated suspension of TiO <sub>2</sub>	Dadjour et al. (2005, 2006)
<i>Microcystis</i>	TiO <sub>2</sub> -coated glass beads	Kim and Lee (2005)
<i>Porphyromonas gingivalis</i>	TiO <sub>2</sub> sol/gel-coated orthodontic wires	Chun et al. (2007)
<i>Prevotella intermedia</i>	Ag-hydroxyapatite-TiO <sub>2</sub> catalyst	Mo et al. (2007)
<i>Proteus vulgaris</i>	P25 (10% Pt), 0.25 g/L slurry	Matsunaga et al. (1985)
<i>P. aeruginosa</i>	Surfaces	Kühn et al. (2003)
<i>P. aeruginosa</i> environmental isolate	Spray-coated soda lime glass and silica tubing	Amezaga-Madrid et al. (2002, 2003)
<i>P. aeruginosa</i> PA01	Thin film	Gage et al. (2005)
<i>P. aeruginosa</i>	Coated Al fibres	Luo et al. (2008)
<i>P. aeruginosa</i>	Catheters	Yao et al. (2008c)
<i>P. fluorescens</i> R2F	TiO <sub>2</sub> pellets	Kerstens et al. (1998)
<i>P. fluorescens</i> B22	Sigma-Aldrich TiO <sub>2</sub> thin films	Skorb et al. (2008)
<i>Pseudomonas</i> sp.	Anodized titanium alloy	Muraleedharan et al. (2003)
<i>Pseudomonas stutzeri</i> NCIMB11358	TiO <sub>2</sub> suspension	Biguzzi and Shama (1994)
<i>Pseudomonas syringae</i> pv tomato	Degussa P25 suspension	Muszkat et al. (2005)
<i>Pseudomonas tolaasi</i>	TiO <sub>2</sub> suspension	Sawada et al. (2005)
<i>Salmonella choleraesuis</i>	Anatase suspension	Kim et al. (2003)
<i>Salmonella enteritidis</i> Typhimurium	Degussa P25 suspension	Ibáñez et al. (2003), Cushnie et al. (2009)
<i>Salmonella enteritidis</i> Typhimurium	TiO <sub>2</sub> film on quartz rods with UVC	Cho et al. (2007a, b)
<i>Serratia marcescens</i>	Degussa P25 suspension	Block et al. (1997)
		Goswami et al. (1999)
<i>Shigella flexneri</i>	C-doped TiO <sub>2</sub>	Cheng et al. (2009)
<i>Vibrio parahaemolyticus</i>	Anatase suspension	Kim et al. (2003)
<i>Vibrio parahaemolyticus</i> VP 144	Anatase TiO <sub>2</sub> dip coated on open porcelain filter cell	Hara-Kudo et al. (2006)
<i>Vibrio vulnificus</i>	TiO <sub>2</sub> -impregnated steel fibres for water treatment	Song et al. (2008)

### Changes in cell permeability

Indirect evidence for membrane damage comes from studies of leakage of cellular components. Saito et al.

(1992) showed that there was a rapid leakage of K<sup>+</sup> from treated cells of *Streptococcus sobrinus* AHT which occurred within 1 min of exposure and paralleled the loss of viability. This was followed by a slower release of RNA

**Table 4** Gram-positive bacteria shown to be killed by photocatalytic disinfection

Organism	Notes	Reference
<i>Actinobacillus actinomycetemcomitans</i>	TiO <sub>2</sub> coating on titanium	Suketa et al. (2005)
<i>Actinomyces viscosus</i>	Kobe Steel TiO <sub>2</sub> 99.98% anatase	Nagame et al. (1989)
<i>Bacillus cereus</i>	TiO <sub>2</sub> suspension	Cho et al. (2007a)
<i>Bacillus cereus</i> spores	TiO <sub>2</sub> suspension	Armon et al. (2004)
<i>Bacillus megaterium</i> QM B1551	Colloidal suspension of TiO <sub>2</sub>	Fu et al. (2005)
<i>Bacillus pumilis</i> spores ATCC 27142	TiO <sub>2</sub> anatase 99.9% slurry in Petri dish	Pham et al. (1995, 1997)
<i>Bacillus</i> sp.	Degussa P-25 immobilised on Pyrex glass	Rincón and Pulgarin (2005)
<i>Bacillus subtilis</i> vegetative cells and endospores	Degussa P25-coated quartz discs	Wolfrum et al. (2002)
<i>Bacillus subtilis</i> endospores	Aluminium foil coated with TiO <sub>2</sub>	Greist et al. (2002)
<i>Bacillus thuringiensis</i>	100% anatase thin film ± Pt doping	Kozlova et al. (2010)
<i>Clavibacter michiganensis</i>	Solar + H <sub>2</sub> O <sub>2</sub>	Muszkat et al. (2005)
<i>Clostridium difficile</i>	Evonik Aeroxide P25 thin film	Dunlop et al. (2010)
<i>Clostridium perfringens</i> spores NCIMB 6125	TiO <sub>2</sub> film on metal electrode	Butterfield et al. (1997)
<i>Clostridium perfringens</i> spores	Degussa P-25 + UVC	Guimarães and Barretto (2003)
<i>Deinococcus radiophilus</i>	TiO <sub>2</sub> suspension	Laot et al. (1999)
<i>Enterococcus (Streptococcus) faecalis</i>	Degussa P25 suspension	Herrera Melián et al. (2000)
<i>Enterococcus (Streptococcus) faecalis</i>	Immobilised TiO <sub>2</sub>	Singh et al. (2005)
<i>Enterococcus faecalis</i> CECT 481	Degussa P25 suspension	Vidal et al. (1999)
<i>Enterococcus faecium</i>	Degussa P25-coated Plexiglass	Kühn et al. (2003)
<i>Enterococcus hirae</i>	TiO <sub>2</sub> on orthopaedic implants	Tsuang et al. (2008)
<i>Enterococcus</i> sp.	Degussa P-25 suspension	Rincón and Pulgarin (2005)
<i>Lactobacillus acidophilus</i>	Degussa P25 suspension	Matsunaga et al. (1985), Choi et al. (2007a)
<i>Lactobacillus helveticus</i> CCRC 13936	TiO <sub>2</sub> suspension	Liu and Yang (2003)
<i>Lactococcus lactis</i> 411	Sigma-Aldrich TiO <sub>2</sub> thin films	Skorb et al. (2008)
<i>Listeria monocytogenes</i>	TiO <sub>2</sub> (Yakuri Pure Chemical Company, Japan) suspension	Kim et al. (2003)
<i>Microbacterium</i> sp. Microbacteriaceae str. W7	Degussa P25 immobilised on membrane	Pal et al. (2007)
<i>Micrococcus luteus</i>	Degussa P25 thick film	Wolfrum et al. (2002)
<i>Micrococcus lylae</i>	TiO <sub>2</sub> suspension	Yu et al. (2005b)
MRSA	Fe <sub>3</sub> O <sub>4</sub> -TiO <sub>2</sub> core/shell magnetic nanoparticles in suspension	Chen et al. (2008)
MRSA	TiO <sub>2</sub> thin film on titanium	Oka et al. (2008)
<i>Mycobacterium smegmatis</i>	100% anatase thin film ± Pt doping	Kozlova et al. (2010)
<i>Porphyromonas gingivalis</i>	TiO <sub>2</sub> thin film on steel and titanium	Shiraishi et al. (1999)
<i>Paenibacillus</i> sp SAFN-007	Degussa P25 immobilised on membrane	Pal et al. (2007)
<i>Staphylococcus aureus</i>	Degussa P25 suspension	Block et al. (1997)
<i>Staphylococcus aureus</i>	TiO <sub>2</sub> thin film on steel and titanium	Shiraishi et al. (1999)
<i>Staphylococcus epidermidis</i> NCTC11047	Ag-TiO <sub>2</sub> catalyst	Sheel et al. (2008)
<i>Staphylococcus saprophyticus</i>	Fe <sub>3</sub> O <sub>4</sub> -TiO <sub>2</sub> core/shell magnetic nanoparticles in suspension	Chen et al. (2008)
<i>Streptococcus cricetus</i>	Kobe Steel TiO <sub>2</sub> 99.98% anatase	Nagame et al. (1989)
<i>Streptococcus iniae</i>	Sol/gel-coated glass slides	Cheng et al. (2008)
<i>Streptococcus mutans</i>	TiO <sub>2</sub> sol/gel-coated orthodontic wires	Chun et al. (2007)
<i>Streptococcus mutans</i> GS5, LM7, OMZ175	P25 aerosil, 70% anatase suspension	Saito et al. (1992)
<i>Streptococcus pyogenes</i> ery <sup>r</sup> cam <sup>r</sup>	Fe <sub>3</sub> O <sub>4</sub> -TiO <sub>2</sub> core/shell magnetic nanoparticles in suspension	Chen et al. (2008)
<i>Streptococcus rattus</i> FA-1	P25 aerosil, 70% anatase suspension	Saito et al. (1992)
<i>Streptococcus sobrinus</i> AHT	P25 suspension	Saito et al. (1992)

**Table 5** Fungi shown to be killed by photocatalytic disinfection

Organism	Notes	Reference
<i>Aspergillus niger</i> AS3315	Wood coated with TiO <sub>2</sub>	Chen et al. (2009)
<i>A. niger</i> spores	Degussa P25 film on quartz discs	Wolfrum et al. (2002)
<i>Aspergillus niger</i>	Thin films of TiO <sub>2</sub> on glass plates	Erkan et al. (2006)
<i>Candida albicans</i> ATCC 10231	Degussa P25 suspension	Lonnen et al. (2005)
<i>Candida albicans</i>	TiO <sub>2</sub> -coated surfaces	Kühn et al. (2003)
<i>Candida famata</i>	TiO <sub>2</sub> coated catheters	Yao et al. (2008c)
<i>Candida vini</i>	TiO <sub>2</sub> thin film	Veselá et al. (2008)
<i>Cladobotryum varium</i>	TiO <sub>2</sub> suspension	Sawada et al. (2005)
<i>Cladosporium cladosporioides</i>	TiO <sub>2</sub> -coated concrete	Giannantonio et al. (2009)
<i>Diaporthe actinidae</i>	TiO <sub>2</sub> immobilised on alumina spheres	Hur et al. (2005)
<i>Erysiphe cichoracearum</i>	Degussa P25 and Ce <sup>3+</sup> doped catalyts	Lu et al. (2006)
<i>Epicoccum nigrum</i>	TiO <sub>2</sub> coated concrete	Giannantonio et al. (2009)
Fungi from spinach	Plastic fruit containers with TiO <sub>2</sub> coating	Koide and Nonami (2007)
<i>Fusarium mucor</i>	TiO <sub>2</sub> -coated concrete	Giannantonio et al. (2009)
<i>Fusarium solani</i> ATCC 36031	Degussa P25 suspension	Lonnen et al. (2005)
<i>Fusarium</i> spp. ( <i>equisetii</i> , <i>oxyartan</i> , <i>anthophilum</i> , <i>verticilloides</i> , <i>solani</i> )	TiO <sub>2</sub> suspension, solar irradiation	Sichel et al. (2007b, c)
<i>Hanseula anomala</i> CCY-138-30	TiO <sub>2</sub> - and Ag-doped	Veselá et al. (2008)
<i>Peronophythora litchii</i>	Degussa P25- and Ce <sup>3+</sup> -doped catalyts	Lu et al. (2006)
<i>Penicillium citrinum</i>	TiO <sub>2</sub> -coated air filter	Lin and Li (2003a, b)
<i>Penicillium expansum</i>	TiO <sub>2</sub> spray coated on polypropylene film	Maneerat and Hayata (2006)
<i>Penicillium oxalicum</i>	TiO <sub>2</sub> -coated concrete	Giannantonio et al. (2009)
<i>Pestotiopsis maculans</i>	TiO <sub>2</sub> -coated concrete	Giannantonio et al. (2009)
<i>Saccharomyces cerevisiae</i>	Aerosil P25 suspension	Matsunaga et al. (1985)
<i>Sacchararomyces cerevisiae</i>	Pd-doped TiO <sub>2</sub>	Erkan et al. (2006)
<i>Spicellum roseum</i>	TiO <sub>2</sub> suspension	Sawada et al. (2005)
<i>Trichoderma asperellum</i>	TiO <sub>2</sub> -coated concrete	Giannantonio et al. (2009)
<i>Trichoderma harzianum</i>	TiO <sub>2</sub> suspension	Sawada et al. (2005)

and protein. Leakage of K<sup>+</sup> was also shown to parallel cell death of *E. coli* (Hu et al. 2007; Kambala and Naidu 2009). Huang et al. (2000) showed an initial increase in permeability to small molecules such as ONPG which was followed by leakage of large molecules such as β-D-galactosidase from treated cells of *E. coli*, suggesting a progressive increase in membrane permeability. Membrane damage has been shown with cells labelled with the LIVE-DEAD® BacLight™ Bacterial Viability Kit which uses the fluorescent dyes Cyto 9, which stains all cells green, and propidium iodide, which only penetrates cells with damaged membranes and stains cells red. Gogniat et al. (2006) showed that permeability changes occurred in the membrane soon after attachment of *E. coli* to the TiO<sub>2</sub>, and we have seen similar changes (Ditta and Foster, unpublished). However, no damage was detected on a visible light active PdO/TiON catalyst until the catalyst had been irradiated (Wu et al. 2010b). SEM clearly showed membrane damage after irradiation on this catalyst (Wu et al. 2008, 2009a, b, 2010b; see Fig. 2).

#### Microscopic changes during PCD

TEM images of treated cells of *S. sobrinus* showed clearly that the cell wall was partially broken after cells had undergone TiO<sub>2</sub> photocatalytic treatment for 60 min, with further disruption after 120 min (Saito et al. 1992). The authors suggested that cell death was caused by alterations in cell permeability and the decomposition of the cell wall. SEM images of *S. aureus*, MRSA, *E. coli* and *M. luteus* showed morphological changes suggestive of cell wall disruption after UVA irradiation on apatite-coated TiO<sub>2</sub> on cotton fabrics (Kangwansupamonkon et al. 2009).

Damage to the cell wall of *P. aeruginosa* was shown by SEM and TEM, which showed changes in membrane structure such as “bubble-like protuberances which expelled cellular material” (Fig. 3; Amezaga-Madrid et al. 2002, 2003). They suggested that leakage of cellular material, and possibly abnormal cell division, was occurring, although the bubbles may have been due to localised



**Table 6** Protozoa and algae shown to be killed by photocatalytic disinfection

Organism	Notes	Reference
Protozoa		
<i>Acanthamoeba castellanii</i>	Degussa P25 suspension Only 50% kill for cysts, trophozoites were sensitive	Sökmen et al. (2008)
<i>Acanthamoeba polyphaga</i> environmental isolate	Degussa P25 suspension	Lonnen et al. (2005)
<i>Cryptosporidium parvum</i>	UVC + TiO <sub>2</sub>	Ryu et al. (2008)
<i>Cryptosporidium parvum</i>	Sol-gel and thermal TiO <sub>2</sub> thin films applied to Petri dish with a counter electrode Pt mesh	Curtis et al. (2002)
<i>Giardia</i> sp.	Fibrous ceramic TiO <sub>2</sub> filter	Navalon et al. (2009)
<i>Giardia intestinalis</i> cysts	TiO <sub>2</sub> (anatase 99.9%) + Ag <sup>+</sup>	Sökmen et al. (2008)
<i>Giardia lamblia</i>	TiO <sub>2</sub> thin film catalyst	Lee et al. (2004)
<i>Tetrahymena pyriformis</i>	TiO <sub>2</sub> suspension	Peng et al. (2010)
Algae		
<i>Amphidinium corterae</i>	Ag-TiO <sub>2</sub> catalyst	Rodriguez-Gonzalez et al. (2010)
<i>Chlorella vulgaris</i>	TiO <sub>2</sub> -Pt catalyst	Matsunaga et al. (1985)
<i>Cladophora</i> sp.	TiO <sub>2</sub> -covered glass beads	Peller et al. (2007)
<i>Chroococcus</i> sp. 27269	Anatase, fluorescent light	Hong et al. (2005)
<i>Melosira</i> sp.	TiO <sub>2</sub> -coated glass beads	Kim and Lee (2005)
<i>Oedogonium</i> sp.	TiO <sub>2</sub> -coated concrete	Linkous et al. (2000)
<i>Tetraselmis suecica</i>	Ag-TiO <sub>2</sub> catalyst	Rodriguez-Gonzalez et al. (2010)

damage to the peptidoglycan layer allowing the inner membrane to bulge through the peptidoglycan layer. Sunada et al. (2003b) studied killing of *E. coli* on thin films of TiO<sub>2</sub> and showed that the outer membrane was

damaged first and then the cytoplasmic membrane followed by complete degradation. Photocatalytic killing occurred without substantial visible degradation of peptidoglycan. Atomic force microscopy measurements of cells on

**Table 7** Viruses shown to be killed by photocatalytic disinfection

Host	Virus	Reference
<i>Bacteroides fragilis</i>	Not specified	Armon et al. (1998)
Birds	Influenza (avian) A/H5N2	Guillard et al. (2008)
<i>E. coli</i>	Coliphage	Guimarães and Barretto (2003)
<i>E. coli</i>	<i>φ</i> r	Gerrity et al. (2008)
<i>E. coli</i>	T4	Ditta et al. (2008), Sheel et al. (2008)
<i>E. coli</i>	λ vir	Yu et al. (2008)
<i>E. coli</i>	λNM1149	Belhácová et al. (1999)
<i>E. coli</i>	φX174	Gerrity et al. (2008)
<i>E. coli</i>	MS2	Sjogren and Sierka (1994), Greist et al. (2002), Cho et al. (2004, 2005), Sato and Taya (2006a, b), Vohra et al. (2006), Gerrity et al. (2008)
<i>E. coli</i>	Qβ	Lee et al. (1997), Otaki et al. (2000)
Human	Hepatitis B virus surface antigen HBsAg	Zan et al. (2007)
Human	Influenza A/H1N1	Lin et al. (2006)
Human	Influenza A/H3N2	Kozlova et al. (2010)
Human	Norovirus	Kato et al. (2005)
Human	<i>Poliovirus</i> type 1 (ATCC VFR-192)	Watts et al. (1995)
Human	SARS coronavirus	Han et al. (2004)
Human	Vaccinia	Kozlova et al. (2010)
<i>Lactobacillus casei</i>	PL-1	Kakita et al. (1997, 2000), Kashige et al. (2001)
<i>Salmonella typhimurium</i>	PRD1	Gerrity et al. (2008)

**Table 8** Microbial toxins inactivated by photocatalysis

Toxin	Publication
Brevetoxins	Khan et al. (2010)
Cylindrospermopsin	Senogles et al. (2000, 2001)
Lipopolysaccharide endotoxin	Sunada et al. (1998)
Microcystin-LR	Lawton et al. (1999, 2003) Cornish et al. (2000) Feitz and Waite (2003) Choi et al. (2007b)
Microcystins LR, YA and YR	Shephard et al. (1998)
Nodularin	Liu et al. (2005)

illuminated TiO<sub>2</sub> film showed that the outer membrane decomposed first (Sunada et al. 2003b).

TEM images showed progressive destruction of *E. coli* cells on Ag/AgBr/TiO<sub>2</sub> in suspension (Hu et al. 2006). Cell membrane was degraded first followed by penetration of TiO<sub>2</sub> particles into the cell and further damage. TEM of *E. coli* showed that there were changes to the nucleoid which became condensed, possibly due to leakage of ions out of the cell (Chung et al. 2009).


TEM of thin sections of treated cells of *E. coli* on a visible light-activated TiO<sub>2</sub> showed various degrees of cell disruption including plasmolysis, intracellular vacuoles ghost and cell debris (Vacaroiu et al. 2009). SEM and TEM studies showed initial swelling and rough appearance of the cells followed by scars and holes in the OM,

especially where the TiO<sub>2</sub> particles were in contact with the cells. Erdem et al. (2006) showed damage by SEM on *E. coli* and production of membrane breakdown products. SEM has shown changes to the outer membrane of *E. coli* (Li et al. 2008; Shah et al. 2008; Gartner et al. 2009). TEM of thin sections of treated cells of *E. coli* on a visible light-activated TiO<sub>2</sub> showed various degrees of cell disruption including plasmolysis, intracellular vacuoles ghost and cell debris (Vacaroiu et al. 2009).


Atomic force microscopy was used to show membrane damage to *E. coli*, *S. aureus* and *Diplococcus (Streptococcus) pneumoniae* on thin films of TiO<sub>2</sub> (Miron et al. 2005). Changes to treated cells of *S. aureus* seen by TEM included separation of cytoplasmic membrane from the peptidoglycan layer (Chung et al. 2009). Distortion of treated cells of both MRSA and methicillin-sensitive *S. aureus* was seen by SEM on anatase–brookite (Shah et al. 2008), again suggesting cell wall damage.

Lipid peroxidation by ROS was demonstrated by the release of MDA as a breakdown product, and there was a concurrent loss of membrane respiratory activity measured by reduction of 2,3,5-triphenyltetrazolium chloride (Maness et al. 1999). The demonstration of degradation of *E. coli* endotoxin without substantial degradation of peptidoglycan (Sunada et al. 1998) suggested that in the case of Gram-negative bacteria, cell disruption occurred in the order of OM→PG→IM. However, alterations to the peptidoglycan layer may not be obvious in electron micrographs as peptidoglycan is a highly cross-linked structure and

**Fig. 2** Scanning electron micrographs of photocatalytically treated *E. coli*. **a** Untreated cells. **b, c** Cells after 240 min. **d** Cells after 30 min. Catalyst TiON thin film. From Wu et al. (2010a, b)

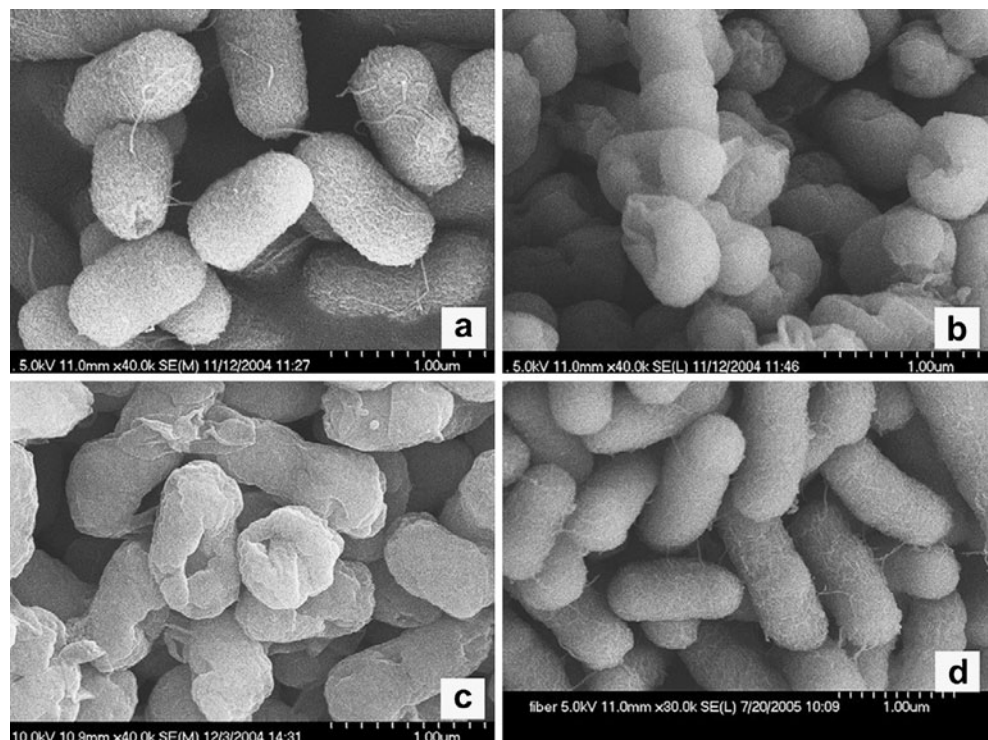

**Fig. 3** Transmission electron micrographs of photocatalytically treated *P. aeruginosa*. Untreated cells transverse section showing normal thickness and shape cell wall (arrows). **b–d** Cells after 240 min treatment showing abnormal wavy cell wall (arrows) (b), cytoplasmic material escaping from the cell with damaged cell wall (arrows) (c) and cell showing two “bubbles” of cellular material with cell wall (arrows) (d). Catalyst TiO<sub>2</sub> thin film. Bar marker=200 nm. From Amezaga-Madrid et al. (2003b)

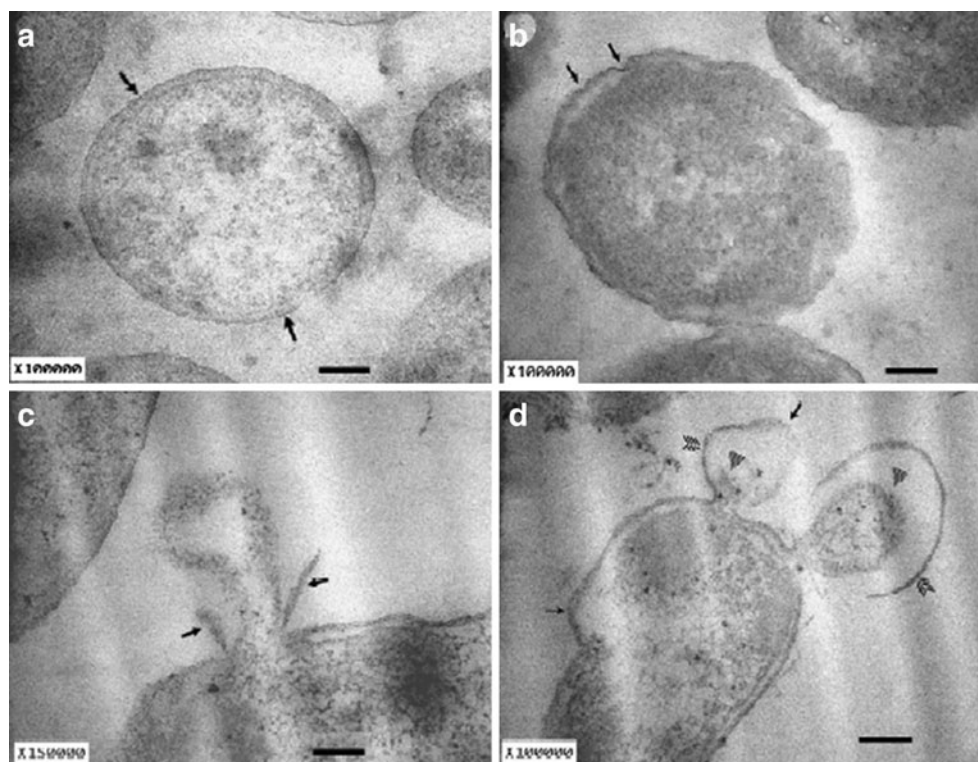


appreciable damage may occur without destruction of its overall appearance. Localised destruction may occur where TiO<sub>2</sub> particles are in contact with the cell. This may allow protrusion of inner membrane through the cell wall as seen by Amezaga-Madrid et al. (2003), followed by total rupture of the cell wall.

Yao et al. (2007c) showed damage to cells of *Erwinia carotovora* and DNA damage, which suggested that damage to DNA was responsible for cell death. However, our own data showed that there was no DNA damage seen by COMET assay on plain TiO<sub>2</sub> surfaces even when 97% of the cells were non-viable (Varghese and Foster, unpublished data; Fig. 4). Damage to DNA does occur on TiO<sub>2</sub> (Wamer et al. 1997; Hirakawa et al. 2004; Wang and Yang 2005; Wang et al. 2005; Gogniat and Dukan 2007; Shen et al. 2008; Yao et al. 2007c; Yang and Wang 2008), but is probably a late event after rupture of the membrane and cell death.

#### Killing of other microorganisms

There have been fewer studies on the mechanism of killing of eukaryotes. Linkous et al. (2000) suggested that death of the alga *Oedogonium* sp. was due to nonspecific breakdown of cellular structures. Microscopy has shown membrane damage to the alga *Chroococcus* sp. (Hong et al. 2005). Light microscopy and SEM showed damage to cell walls of *Candida albicans* suspended over a thin film of TiO<sub>2</sub> (Kühn et al. 2003) and on TiO<sub>2</sub>-coated tissue conditioner (Akiba et al. 2005). Cell wall and membrane

damage to cysts were seen with light microscopy of photocatalytically treated *Giardia lamblia* (Sökmen et al. 2008). Membrane damage was also shown to occur on

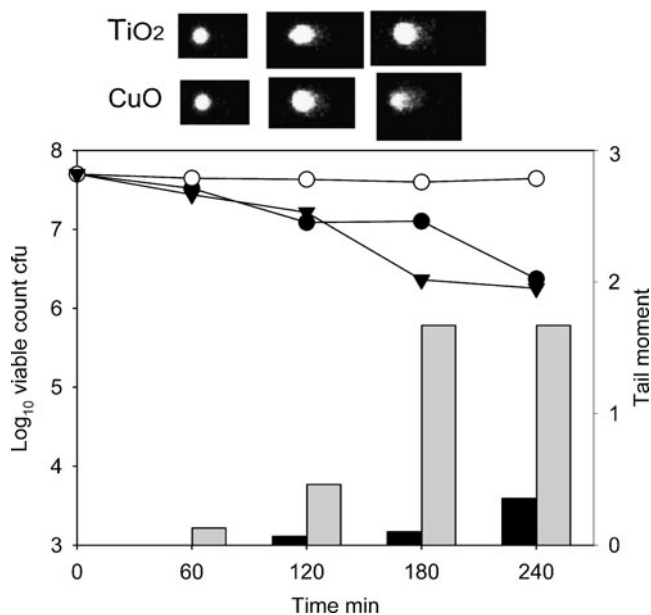

**Fig. 4** Comet assay of DNA from cells of *E. coli* on photoirradiated TiO<sub>2</sub> and CuO–TiO<sub>2</sub> catalysts. Upper photographs show fragmented DNA entering the gel like the tail of a comet. The graph shows viability (control, open circle; TiO<sub>2</sub> catalyst, closed circle; TiO<sub>2</sub>–CuO dual catalyst, downturned triangle) and tail moment (TM = Tail length × % DNA in tail/100; Olive et al. 1990) as the measure of the extent of DNA damage (TiO<sub>2</sub> catalyst, black square; TiO<sub>2</sub>–CuO dual catalyst, gray square) against time

treatment of the ciliate protozoan *Tetrahymena pyriformis* (Peng et al. 2010).

Killing of *Lactobacillus* phage PL1 by thin films of TiO<sub>2</sub> suspended in liquid was reported to be via initial damage to protein of the capsid by ·OH, followed by damage to the phage DNA inside the particles (Kashige et al. 2001). SEM showed ghost particles and empty heads. Damage to the H and N projections of influenza virus A/H1N1 occurred on PCD and was followed by total mineralisation (Lin et al. 2006).

### Spectroscopic studies

The activity of titanium dioxide on isolated phospholipid bilayers has been shown to result in disruption of the bilayer structure using X-ray diffraction (Suwalsky et al. 2005), laser kinetic spectroscopy and attenuated total reflection Fourier transform infrared spectroscopy (FTIR). Disruption was shown to be due to lipid peroxidation (Kiwi and Nadochenko 2004; Nadochenko et al. 2006) measured by production of malondialdehyde (MDA). Lipid peroxidation occurs when polyunsaturated fatty acids such as linoleic acid are attacked by ROS (Kiwi and Nadochenko 2005).


FTIR spectra of treated *E. coli* confirmed the production of carboxylic acids such as MDA as products of membrane degradation. MDA was further degraded by longer irradiation times (Hu et al. 2007).

The electron decay on TiO<sub>2</sub> was studied using laser kinetic spectroscopy in the presence of phosphatidyl ethanolamine, lipopolysaccharide and *E. coli* (Nadochenko et al. 2006). Spectroscopic studies using FTIR spectroscopy suggested that organic components bound to the TiO<sub>2</sub> were directly oxidised by reduction of the electron holes (Nadochenko et al. 2006, 2008). This work suggested that direct oxidation of cellular components could occur without the production of ROS, but only if cells were in direct contact with the surface of the TiO<sub>2</sub>. This is wholly consistent with the greater effectiveness of PCD when the cells are in contact with the TiO<sub>2</sub> rather than in suspension. Overall, the spectroscopic studies support the light microscopic studies and confirm the order of destruction being OM→IM→PG. Details of kinetic models of the killing mechanism are presented by Dalrymple et al. (2010).

The role of ROS in killing of bacteria is summarised in Fig. 5.


### Role of ROS in the killing mechanism

Most studies show that ROS are responsible for the killing, and various authors propose that ·OH are responsible

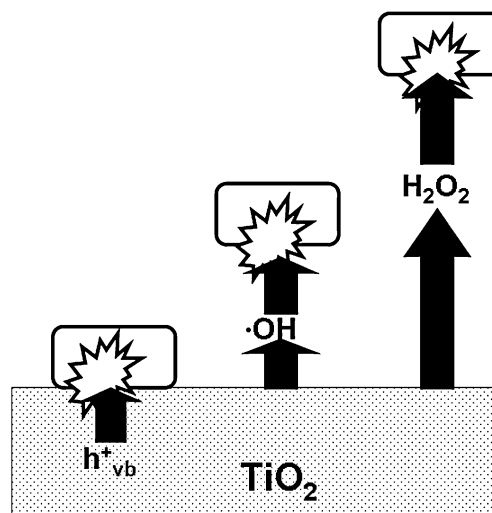

**Fig. 5** Role of ROS in photocatalytic killing of bacteria. Direct oxidation of cell components can occur when cells are in direct contact with the catalyst. Hydroxyl radicals and H<sub>2</sub>O<sub>2</sub> are involved close to and distant from the catalyst, respectively. Furthermore, ·OH can be generated from reduction of metal ions, e.g. Cu<sup>2+</sup> by H<sub>2</sub>O<sub>2</sub> (Sato and Taya 2006c)

(Ireland et al. 1993; Kikuchi et al. 1997; Maness et al. 1999; Salih 2002; Cho et al. 2004, 2005; Cho and Yoon 2008). Lipid peroxidation by ROS was demonstrated by the release of MDA as a breakdown product, and there was a concurrent loss of membrane respiratory activity measured by reduction of 2,3,5-triphenyltetrazolium chloride (Maness et al. 1999). The ·OH scavengers, dimethylsulphoxide and cysteamine, eliminated the PCD activity of suspensions of TiO<sub>2</sub> in water (Salih 2002). However, ·OH are short-lived and will probably not diffuse further than 1 μm from the surface of the TiO<sub>2</sub>, especially in the presence of organic matter (Pryor 1986; Kikuchi et al. 1997). Kikuchi et al. (1997) showed that killing of *E. coli* still occurred even when the bacteria were separated from the surface by a 50-μm-thick porous membrane. However, the free radical scavenger mannitol only inhibited killing without the membrane, whereas catalase, which would degrade H<sub>2</sub>O<sub>2</sub>, decreased killing both with and without the membrane. This suggested that ·OH and H<sub>2</sub>O<sub>2</sub> were responsible for killing close to the TiO<sub>2</sub>, with H<sub>2</sub>O<sub>2</sub> acting at a distance. The role of other ROS, e.g. O<sub>2</sub><sup>·-</sup> was not considered. However, no killing was seen when cells were separated from the TiO<sub>2</sub> by a dialysis membrane in a separate study (Guillard et al. 2008). Hydrogen peroxide may act at a distance if ferrous ions are present by producing ·OH via the Fenton reaction (8 and 9).



A study of the roles of  $\text{H}_2\text{O}_2$  and  $\cdot\text{OH}$  in an immobilised  $\text{TiO}_2$  thin film reactor activated by UVC using electron spin resonance suggested that  $\cdot\text{OH}$  were produced by direct photolysis of  $\text{H}_2\text{O}_2$  as well as by Eqs. 3 and 4 (Yan et al. 2009).

A role for  $\cdot\text{OH}$  in sonocatalysis on  $\text{TiO}_2$  (where the energy to bridge the band gap is provided by sound waves) was suggested by the work of Ogino et al. 2006 who showed that the killing was inhibited by the  $\cdot\text{OH}$  scavenger glutathione. Hydroxyl radicals produced by microwave irradiation of  $\text{TiO}_2$  were shown to enhance the killing of *E. coli* (Takashima et al. 2007).

Hydroxyl radicals were shown to be the major ROS involved in killing of *C. parvum* cysts, although other ROS were also involved (Cho and Yoon 2008).

Studies with hydroxyl radical scavengers suggested that inactivation of phage in suspensions of  $\text{TiO}_2$  also occurred due to bulk phase  $\cdot\text{OH}$ , whereas inactivation of bacteria occurred with both bulk phase and surface  $\cdot\text{OH}$  (Cho et al. 2004, 2005). The rate of inactivation of *E. coli* correlated with the concentration of  $\cdot\text{OH}$ . A role for other ROS such as  $\text{H}_2\text{O}_2$  and  $\text{O}_2\cdot^-$  was also suggested.

Studies on superoxide dismutase (SOD)-defective *E. coli* have shown that oxidative damage to the membrane combined with the turgor pressure inside the cell initially permeabilizes the cell envelope, allowing critical metabolites to escape (Imlay and Fridovich 1992). Studies on oxidative damage caused by  $\text{TiO}_2$  in SOD mutants of *E. coli* showed that the inactivation rate was inversely proportional to SOD activity (Koizumi et al. 2002; Kim et al. 2004).


Kinetic models and further details of the chemistry of the killing mechanism are presented by Dalrymple et al. (2010). The role of  $h_{\nu b}^+$  and ROS in killing of bacteria is summarised in Fig. 5.

### Importance of contact between bacteria and $\text{TiO}_2$

Many studies have shown that close contact between the bacteria and the  $\text{TiO}_2$  increases the extent of oxidative damage. Studies on the disinfection of water have shown that suspended  $\text{TiO}_2$  is more active than  $\text{TiO}_2$  immobilised on surfaces, e.g. on thin films (Lee et al. 1997; Otaki et al. 2000; Sun et al. 2003; Gumy et al. 2006b; Marugan et al. 2006, 2008; Cohen-Yaniv et al. 2008). This is probably due to increased contact between the  $\text{TiO}_2$  particles and the bacterial cells in suspension as well as an increased surface area for ROS production. A number of studies confirm the importance of such contact (Horie et al. 1996a, b, 1998; Gumy et al. 2006a; Pratap Reddy et al. 2008; Caballero et al. 2009; Cheng et al. 2009). Co-precipitation of cells and  $\text{TiO}_2$  particles from suspension

by alum enhanced killing of *E. coli* (Salih 2004). Certain ionic species have been shown to inhibit PCD, e.g.  $\text{PO}_4^{3-}$  (Araña et al. 2002; Koizumi and Taya 2002a,b; Christensen et al. 2003; Rincón and Pulgarin 2004b; Egerton et al. 2006; Xiong et al. 2006; Marugan et al. 2008) and  $\text{HCO}_3^-$  (Rincón and Pulgarin 2004b; Coleman et al. 2005; Gogniat et al. 2006), and the rate of adsorption onto the  $\text{TiO}_2$  in the presence of different ions correlated with the rate of inactivation, suggesting that the inhibition was due to the prevention of binding of the bacteria to the  $\text{TiO}_2$  particles. Light micrographs (Nadtochenko et al. 2005; Gumy et al. 2006b; Gogniat et al. 2006) and electron micrographs clearly show binding of the titania particles to bacterial cells (Gumy et al. 2006a, b; Saito et al. 1992; Cheng et al. 2007; Shah et al. 2008). A micrograph showing particles of  $\text{TiO}_2$  attached to an *E. coli* cell is shown in Fig. 6. Contact with highly crystalline  $\text{TiO}_2$  may also cause physical damage to the cells (Liu et al. 2007c; Caballero et al. 2009).

Although differences in binding of isolated O antigens to  $\text{TiO}_2$  have been shown (*E. coli* O8 and *Citrobacter freundii* O antigens bound strongly to  $\text{TiO}_2$ , whereas that from *Stenotrophomonas maltophilia* had a low affinity for  $\text{TiO}_2$ ; Jucker et al. 1997), differences in the susceptibility of bacteria with different O antigens have not been studied. Differences in the susceptibility of different strains of *Legionella pneumophila* correlated with the amount of saturated 16C branched chain fatty acids in the membrane (Cheng et al. 2007). The more hydrophobic cells of

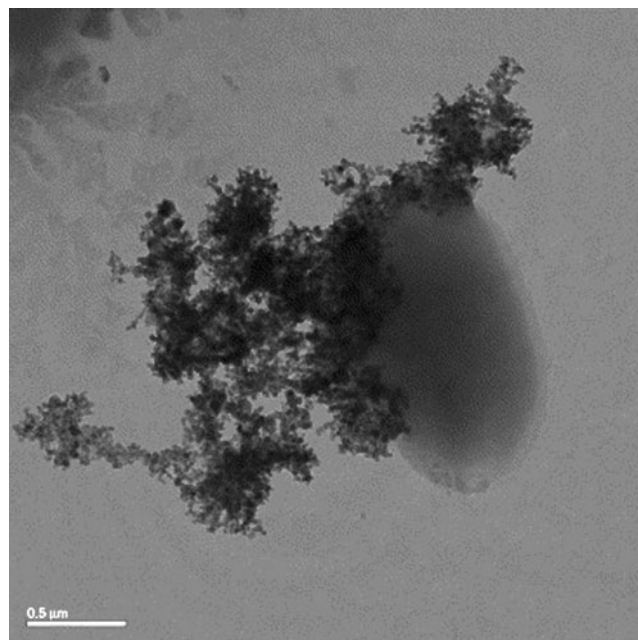

**Fig. 6** Transmission electron micrograph of *E. coli* showing adhesion between cells and  $\text{TiO}_2$  in suspension. Catalyst Degussa P25 pH 6.0. From Gumy et al. (2006b)

*Flavobacterium* sp. were more easily killed by PCD than *E. coli* (Cohen-Yaniv et al. 2008), which may also have been due to altered interactions with the TiO<sub>2</sub>.


In an attempt to increase contact between the cells, Benabbou et al. (2007) studied the PCD of a strain of *E. coli* overexpressing *curli*, pili, which enhance adhesion to abiotic surfaces. However, the strain was more resistant than the non-piliated control, and evidence of protein degradation suggested that the pili were being degraded before the membrane was damaged and therefore protected the membrane from damage. The presence of extracellular polysaccharides interfered with PCD of biofilms of *P. aeruginosa* (Gage et al. 2005) and a natural biofilm (Liu et al. 2007a), but killing was seen throughout a biofilm of *Staphylococcus epidermidis* on a TiO<sub>2</sub> catalyst (Dunlop et al. 2010). The different biofilms and catalysts may explain these anomalies.

The inhibition of close contact between coliphage MS2 and TiO<sub>2</sub> by certain cations was shown by Koizumi and Taya (2002a, b), and the rate of inactivation was proportional to adsorption of the phage onto the TiO<sub>2</sub>. Sato and Taya (2006a, b) showed that the presence of organic materials protected the phage by adsorbing to the surface of the TiO<sub>2</sub>, preventing phage binding.

### Cell mineralisation

Following initial cell damage and cell death, photocatalysis has been shown to be capable of complete mineralisation of bacteria on air filters using <sup>14</sup>C-labelled cells (Jacoby et al. 1998; Wolfrum et al. 2002) and for cells suspended in water (Cooper et al. 1997; Sökmen et al. 2001). The total oxidation of *Legionella* by PCO was measured by total organic carbon analysis (Cheng et al. 2007). An almost complete degradation of *E. coli* was demonstrated on prolonged treatment on a TiO<sub>2</sub>-activated charcoal catalyst (Li et al. 2008). Nadochenko et al. (2008) showed total oxidation of cell organic matter by total internal reflection/FTIR. Removal of microorganisms during regeneration of photocatalytic TiO<sub>2</sub>-coated air filters by complete removal of contaminants has also been shown by SEM (Goswami et al. 1999; Ortiz López and Jacoby 2002). Penetration of TiO<sub>2</sub> particles into the cells was shown using an Ag/AgBr/TiO<sub>2</sub> catalyst (Hu et al. 2006).

A scheme for the killing mechanism of TiO<sub>2</sub> on bacteria is shown in Fig. 7. We suggest that there may be initial damage on contact between the cells and TiO<sub>2</sub> which affects membrane permeability, but is reversible. This is followed by increased damage to all cell wall layers, allowing leakage of small molecules such as ions. Damage at this stage may be irreversible, and this accompanies cell death. As the peptidoglycan is a highly

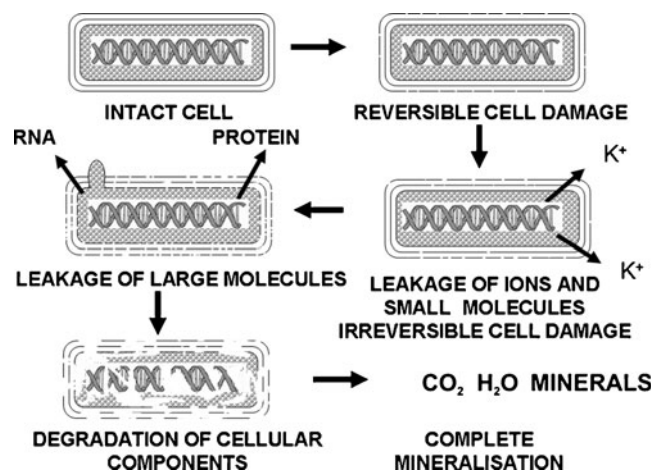

**Fig. 7** Scheme for photocatalytic killing and destruction of bacteria on TiO<sub>2</sub>. Contact between the cells and TiO<sub>2</sub> may affect membrane permeability, but is reversible. This is followed by increased damage to all cell wall layers, allowing leakage of small molecules such as ions. Damage at this stage may be irreversible, and this accompanies cell death. Furthermore, membrane damage allows leakage of higher molecular weight components such as proteins, which may be followed by protrusion of the cytoplasmic membrane into the surrounding medium through degraded areas of the peptidoglycan and lysis of the cell. Degradation of the internal components of the cell then occurs, followed by complete mineralisation. The degradation process may occur progressively from the side of the cell in contact with the catalyst

cross-linked molecule, damage may not be visibly evident at this stage or may be localised if the TiO<sub>2</sub> is in contact with the cells. Further membrane damage allows leakage of higher molecular weight components such as proteins. This may be followed by protrusion of the cytoplasmic membrane into the surrounding medium through degraded areas of the peptidoglycan and, eventually, lysis of the cell. Degradation of the internal components of the cell can then occur followed by complete mineralisation.


### Dual function materials

Copper-deposited films show enhanced PCD activity (Sunada et al. 2003a; Foster et al. 2010; Wu et al. 2010a; Yates et al. 2008a, b). A clear synergy in photokilling of *E. coli* on Cu-containing TiO<sub>2</sub> films was shown by Sato and Taya (2006c) who showed that H<sub>2</sub>O<sub>2</sub> was produced from the photocatalyst and Cu<sup>2+</sup> leached from the surface, but neither reached high enough concentrations to kill the *E. coli* directly. They suggested that the Cu<sup>2+</sup> was reduced to Cu<sup>+</sup> (10) which reacted with the H<sub>2</sub>O<sub>2</sub> to produce ·OH via a Fenton-type reaction (11), which was responsible for killing cells in suspension and explaining why catalase reduced this activity. Inclusion of Cu also gave higher PC activity, hence the enhanced killing of cells bound to the TiO<sub>2</sub>. In our own work, we have seen DNA damage when TiO<sub>2</sub>/

CuO surfaces were used (Fig. 4). Thus, Cu may also kill cells by DNA damage as well as membrane damage. This is consistent with the observed enhancement of damage to DNA and protein caused by ROS (Cervantes-Cervantes et al. 2005).



Similar synergy has been shown between Ag and TiO<sub>2</sub>. Ag enhances photocatalysis by enhancing charge separation at the surface of the TiO<sub>2</sub> (Sökmen et al. 2001; He et al. 2002; Hirakawa and Kamat 2005; Kubacka et al. 2008b; Liu et al. 2007b; Musil et al. 2009). Ag<sup>+</sup> is antimicrobial and can also enhance generation of ROS (Eqs. 12, 13 and 14).



## Conclusions

Generation of ROS by photocatalysis on TiO<sub>2</sub> is capable of killing a wide range of organisms including bacteria endospores in water, in air and on surfaces, including various materials. The technology has the potential to provide a powerful weapon in the fight against transmission of infectious diseases, particularly in view of the development of visible light-activated catalysts.

One of the problems is that until relatively recently, there has not been an accepted standard method for the testing of the antimicrobial efficiency of photocatalytic processes. For example, many different strains of *E. coli* have been used (Table 2) with different growth media and test conditions. This makes it very difficult to compare results from different research groups. In the second part of this review, we will investigate the evaluation of photocatalytic killing activity.

**Acknowledgements** The authors are grateful to Professor David Sheel and Dr. Heather Yates of the Centre for Physics and Materials Research, University of Salford and to CVD Technologies Ltd. for production of titania films and for their comments on the manuscript. We would also like to thank Mr. Roger Bickley for his advice on the early literature on TiO<sub>2</sub>. This work was partly supported by EEC Framework 7 grant CP-IP 214134-2 N2P "Nano-to Production".

## References

- Akiba N, Hayakawa I, Keh ES, Watanabe A (2005) Antifungal effects of a tissue conditioner coating agent with TiO<sub>2</sub> photocatalyst. *J Med Dent Sci* 52(4):223–227
- Allen NS, Edge M, Verran J, Stratton J, Maltby J, Bygott C (2008) Photocatalytic titania based surfaces: environmental benefits. *Polym Degrad Stab* 93(9):1632–1646
- Amezaga-Madrid P, Nevarez-Moorillon GV, Orrantia-Borunda E, Miki-Yoshida M (2002) Photoinduced bactericidal activity against *Pseudomonas aeruginosa* by TiO<sub>2</sub> based thin films. *FEMS Microbiol Lett* 211(2):183–188
- Amezaga-Madrid P, Silveyra-Morales R, Cordoba-Fierro L, Nevarez-Moorillon GV, Miki-Yoshida M, Orrantia-Borunda E, Solis FJ (2003) TEM evidence of ultrastructural alteration on *Pseudomonas aeruginosa* by photocatalytic TiO<sub>2</sub> thin films. *J Photochem Photobiol B* 70(1):45–50. doi:10.1016/s1011-1344(03)00054-x
- Araña J, Herrera Melián JA, Doña Rodríguez JM, González Díaz O, Viera A, Pérez Peña J, Marrero Sosa PM, Espino Jiménez V (2002) TiO<sub>2</sub>-photocatalysis as a tertiary treatment of naturally treated wastewater. *Catal Today* 76(2–4):279–289
- Armon R, Laot N, Narkis N, Neeman I (1998) Photocatalytic inactivation of different bacteria and bacteriophages in drinking water at different TiO<sub>2</sub> concentrations with or without exposure to O<sub>2</sub>. *J Adv Oxid Technol* 3:145–150
- Armon R, Weltch-Cohen G, Bettane P (2004) Disinfection of *Bacillus* spp. spores in drinking water by TiO<sub>2</sub> photocatalysis as a model for *Bacillus anthracis*. *Waterborne Pathog* 4(2):7–14
- Bai S, Mo A, Xian S, Zuo Y, Li Y, Xu W (2007) Characterization and antibacterial effect of a novel nanocomposite membrane. *Bio-ceramics 19* published in *Key Eng Mater* 330–332(I):325–328
- Bekbölet M (1997) Photocatalytic bactericidal activity of TiO<sub>2</sub> in aqueous suspensions of E-coli. *Water Sci Technol* 35:95–100
- Bekbölet M, Araz CV (1996) Inactivation of *Escherichia coli* by photocatalytic oxidation. *Chemosphere* 32(5):959–965
- Belhácová L, Krýsa J, Geryk J, Jirkovský J (1999) Inactivation of microorganisms in a flow-through photoreactor with an immobilized TiO<sub>2</sub> layer. *J Chem Technol Biotechnol* 74(2):149–154
- Benabbou AK, Derriche Z, Felix C, Lejeune P, Guillard C (2007) Photocatalytic inactivation of *Escherichia coli*—effect of concentration of TiO<sub>2</sub> and microorganism, nature, and intensity of UV irradiation. *Appl Catal B* 76(3–4):257–263. doi:10.1016/j.apcatb.2007.05.026
- Biguzzi M, Shama G (1994) Effect of titanium-dioxide concentration on the survival of *Pseudomonas-stutzeri* during irradiation with near-ultraviolet light. *Lett Appl Microbiol* 19(6):458–460
- Blake DM, Maness PC, Huang Z, Wolfrum EJ, Huang J, Jacoby WA (1999) Application of the photocatalytic chemistry of titanium dioxide to disinfection and the killing of cancer cells. *Sep Purif Methods* 28(1):1–50
- Block SS, Seng VP, Goswami DW (1997) Chemically enhanced sunlight for killing bacteria. *J Sol Energy Eng Trans ASME* 119(1):85–91
- Brook LA, Evans P, Foster HA, Pemble ME, Steele A, Sheel DW, Yates HM (2007) Highly bioactive silver and silver/titania composite films grown by chemical vapour deposition. *J Photochem Photobiol* 187(1):53–63
- Butterfield IM, Christensen PA, Curtis TP, Gunlazuardi J (1997) Water disinfection using an immobilised titanium dioxide film in a photochemical reactor with electric field enhancement. *Water Res* 31(3):675–677
- Caballero L, Whitehead KA, Allen NS, Verran J (2009) Inactivation of *Escherichia coli* on immobilized TiO<sub>2</sub> using fluorescent light. *J Photochem Photobiol A* 202(2–3):92–98. doi:10.1016/j.jphotochem.2008.11.005

- Carey JH, Oliver BG (1980) The photochemical treatment of wastewater by ultraviolet irradiation of semiconductors. *Water Pollut Res J Can* 15(2):157–185
- Carey JH, Lawrence J, Tosine HM (1976) Photodechlorination of PCB's in the presence of titanium dioxide in aqueous suspensions. *Bull Environ Contam Toxicol* 16(6):697–701
- Carp O, Huisman CL, Reller A (2004) Photoinduced reactivity of titanium dioxide. *Prog Solid State Chem* 32:33–177
- Cerrada ML, Serrano C, Sanchez-Chaves M, Fernandez-Garcia M, Fernandez-Martin F, de Andres A, Rioboo RJJ, Kubacka A, Ferrer M (2008) Self-sterilized evoh-TiO<sub>2</sub> nanocomposites: interface effects on biocidal properties. *Adv Funct Mater* 18(13):1949–1960. doi:10.1002/adfm.200701068
- Cervantes-Cervantes MP, Calderon-Salinas JV, Albores A, Munoz-Sanchez JL (2005) Copper increases the damage to DNA and proteins caused by reactive oxygen species. *Biol Trace Elem Res* 103(3):229–248
- Chan DWT, Law KC, Kwan CHS, Chiu WY (2005) Application of an air purification system to control air-borne bacterial contamination in a university clinic. *Trans Hong Kong Inst Eng* 12(1):17–21
- Chawengkijwanich C, Hayata Y (2008) Development of TiO<sub>2</sub> powder-coated food packaging film and its ability to inactivate *Escherichia coli* in vitro and in actual tests. *Int J Food Microbiol* 123(3):288–292. doi:10.1016/j.ijfoodmicro.2007.12.017
- Chen J, Poon C-s (2009) Photocatalytic construction and building materials: from fundamentals to applications. *Build Environ* 44(9):1899–1906
- Chen WJ, Tsai PJ, Chen YC (2008) Functional Fe<sub>3</sub>O<sub>4</sub>/TiO<sub>2</sub> core/shell magnetic nanoparticles as photokilling agents for pathogenic bacteria. *Small* 4(4):485–491
- Chen FN, Yang XD, Wu Q (2009) Antifungal capability of TiO<sub>2</sub> coated film on moist wood. *Build Environ* 44(5):1088–1093. doi:10.1016/j.buildenv.2008.07.018
- Cheng YW, Chan RCY, Wong PK (2007) Disinfection of *Legionella pneumophila* by photocatalytic oxidation. *Wat Res* 41(4):842–852. doi:10.1016/j.watres.2006.11.033
- Cheng TC, Chang CY, Chang CI, Hwang CJ, Hsu HC, Wang DY, Yao KS (2008) Photocatalytic bactericidal effect of TiO<sub>2</sub> film on fish pathogens. *Surf Coat Technol* 203(5–7):925–927. doi:10.1016/j.surfcoat.2008.08.022
- Cheng CL, Sun DS, Chu WC, Tseng YH, Ho HC, Wang JB, Chung PH, Chen JH, Tsai PJ, Lin NT, Yu MS, Chang HH (2009) The effects of the bacterial interaction with visible-light responsive titania photocatalyst on the bactericidal performance. *J Biomed Sci* 16(7):10
- Cho M, Yoon J (2008) Measurement of OH radical ct for inactivating *Cryptosporidium parvum* using photo/ferrioxalate and photo/TiO<sub>2</sub> systems. *J Appl Microbiol* 104(3):759–766. doi:10.1111/j.1365-2672.2007.03682.x
- Cho M, Chung H, Choi W, Yoon J (2004) Linear correlation between inactivation of *E. coli* and OH radical concentration in TiO<sub>2</sub> photocatalytic disinfection. *Wat Res* 38(4):1069–1077
- Cho M, Chung H, Choi W, Yoon J (2005) Different inactivation behaviors of ms-2 phage and *Escherichia coli* in TiO<sub>2</sub> photocatalytic disinfection. *Appl Environ Microbiol* 71(1):270–275
- Cho M, Choi Y, Park H, Kim K, Woo GJ, Park J (2007a) Titanium dioxide/UV photocatalytic disinfection in fresh carrots. *J Food Prot* 70(1):97–101
- Cho DL, Min H, Kim JH, Cha GS, Kim GS, Kim BH, Ohk SH (2007b) Photocatalytic characteristics of TiO<sub>2</sub> thin films deposited by PECVD. *J Ind Eng Chem* 13(3):434–437
- Choi YL, Kim SH, Song YS, Lee DY (2004) Photodecomposition and bactericidal effects of TiO<sub>2</sub> thin films prepared by a magnetron sputtering. *J Mater Sci* 39(18):5695–5699
- Choi JY, Kim KH, Choy KC, Oh KT, Kim KN (2007a) Photocatalytic antibacterial effect of TiO<sub>2</sub> film formed on Ti and TiAg exposed to *Lactobacillus acidophilus*. *J Biomed Mater Res B* 80(2):353–359
- Choi H, Stathatos E, Dionysiou DD (2007b) Photocatalytic TiO<sub>2</sub> films and membranes for the development of efficient wastewater treatment and reuse systems. *Desalin* 202(1–3):199–206. doi:10.1016/j.desal.2005.12.055
- Chong MN, Jin B, Chow CWK, Saint C (2010) Recent developments in photocatalytic water treatment technology: a review. *Wat Res* 44(10):2997–3027
- Christensen PA, Curtis TP, Egerton TA, Kosa SAM, Tinlin JR (2003) Photoelectrocatalytic and photocatalytic disinfection of *E. coli* suspensions by titanium dioxide. *Appl Catal B* 41(4):371–386
- Chun MJ, Shim E, Kho EH, Park KJ, Jung J, Kim JM, Kim B, Lee KH, Cho DL, Bai DH, Lee SI, Hwang HS, Ohk SH (2007) Surface modification of orthodontic wires with photocatalytic titanium oxide for its antiadherent and antibacterial properties. *Ang Orthodont* 77(3):483–488
- Chung CJ, Lin HI, Chou CM, Hsieh PY, Hsiao CH, Shi ZY, He JL (2009) Inactivation of *Staphylococcus aureus* and *Escherichia coli* under various light sources on photocatalytic titanium dioxide thin film. *Surf Coat Technol* 203(8):1081–1085
- Cohen-Yaniv V, Narkis N, Armon R (2008) Photocatalytic inactivation of *Flavobacterium* and *E. coli* in water by a continuous stirred tank reactor (CSTR) fed with suspended/immobilised TiO<sub>2</sub> medium. *Wat Sci Technol* 58(1):247–252. doi:10.2166/wst.2008.664
- Coleman HM, Marquis CP, Scott JA, Chin SS, Amal R (2005) Bactericidal effects of titanium dioxide-based photocatalysts. *Chem Eng J* 113(1):55–63. doi:10.1016/j.cej.2005.07.015
- Cooper AT, Goswami DY, Block SS (1997) Simultaneous detoxification and disinfection of water by solar photocatalytic treatment. *Int Sol Energy Conf* 1997:277–282
- Cornish BIPA, Lawton LA, Robertson PKJ (2000) Hydrogen peroxide enhanced photocatalytic oxidation of microcystin-LR using titanium dioxide. *Appl Catal B* 25(1):59–67
- Curtis TP, Alker GW, Dowling BM, Christensen PA (2002) Fate of *Cryptosporidium* oocysts in an immobilised titanium dioxide reactor with electric field enhancement. *Wat Res* 36(9):2410–2413
- Cushnie TPT, Robertson PKJ, Officer S, Pollard PM, McCullagh C, Robertson JMC (2009) Variables to be considered when assessing the photocatalytic destruction of bacterial pathogens. *Chemosphere* 74(10):1374–1378. doi:10.1016/j.chemosphere.2008.11.012
- Dadjour MF, Ogino C, Matsumura S, Shimizu N (2005) Kinetics of disinfection of *Escherichia coli* by catalytic ultrasonic irradiation with TiO<sub>2</sub>. *Biochem Eng J* 3:243–248. doi:10.1016/j.bej.2005.04.028
- Dadjour MF, Ogino C, Matsumura S, Nakamura S, Shimizu N (2006) Disinfection of *Legionella pneumophila* by ultrasonic treatment with TiO<sub>2</sub>. *Wat Res* 40(6):1137–1142. doi:10.1016/j.watres.2005.12.047
- Dalrymple OK, Stefanakos E, Trotz MA, Goswami DY (2010) A review of the mechanisms and modeling of photocatalytic disinfection. *Appl Catal B* 98(1–2):27–38
- Ditta IB, Steele A, Liptrot C, Tobin J, Tyler H, Yates HM, Sheel DW, Foster HA (2008) Photocatalytic antimicrobial activity of thin surface films of TiO<sub>2</sub>, CuO and TiO<sub>2</sub>/CuO dual layers on *Escherichia coli* and bacteriophage T4. *Appl Microbiol Biotechnol* 79(1):127–133. doi:10.1007/s00253-008-1411-8
- Duffy EF, Al Touati F, Kehoe SC, McLoughlin OA, Gill LW, Gernjak W, Oller I, Maldonado MI, Malato S, Cassidy J, Reed RH, McGuigan KG (2004) A novel TiO<sub>2</sub>-assisted solar photocatalytic batch-process disinfection reactor for the treatment of biological and chemical contaminants in domestic drinking water in developing countries. *Sol Energy* 77(5):649–655. doi:10.1016/j.solener.2004.05.006
- Dunlop PSM, Byrne JA, Manga N, Eggins BR (2002) The photocatalytic removal of bacterial pollutants from drinking water. *J Photochem Photobiol A* 148(1–3):355–363



- Dunlop PSM, Sheeran CP, Byrne JA, McMahon MAS, Boyle MA, McGuigan KG (2010) Inactivation of clinically relevant pathogens by photocatalytic coatings. *J Photochem Photobiol A* 216:303–310
- Egerton TA, Christensen PA, Kosa SAM, Onoka B, Harper JC, Tinlin JR (2006) Photoelectrocatalysis by titanium dioxide for water treatment. *Int J Environ Pollut* 27(1–3):2–19
- Erdem A, Metzler D, Chou HW, Lin HY, Huang CP (2006) Growth and some enzymatic responses of *E. coli* to photocatalytic TiO<sub>2</sub>. 2006 NSTI Nanotechnology Conference and Trade Show—NSTI Nanotech 2006 Technical Proceedings, 2006, pp 588–591
- Erkan A, Bakir U, Karakas G (2006) Photocatalytic microbial inactivation over Pd doped SnO<sub>2</sub> and TiO<sub>2</sub> thin films. *J Photochem Photobiol A* 184(3):313–321. doi:10.1016/j.jphotochem.2006.05.001
- Feitz AJ, Waite TD (2003) Kinetic modeling of TiO<sub>2</sub>-catalyzed photodegradation of trace levels of microcystin-LR. *Environ Sci Technol* 37(3):561–568
- Fernandez P, Blanco J, Sichel C, Malato S (2005) Water disinfection by solar photocatalysis using compound parabolic collectors. *Catal Today* 101(3–4):345–352. doi:10.1016/j.catod.2005.03.062
- Foster HA, Sheel DW, Sheel P, Evans P, Varghese S, Rutschke N, Yates HM (2010) Antimicrobial activity of titania/silver and titania/copper films prepared by CVD. *J Photochem Photobiol A* 216:283–289. doi:10.1016/j.jphotochem.2010.09.017
- Frank SN, Bard AJ (1977) Heterogeneous photocatalytic oxidation of cyanide and sulfite in aqueous solutions at TiO<sub>2</sub> powders. *J Am Chem Soc* 99(1):303–304
- Fu GF, Vary PS, Lin CT (2005) Anatase TiO<sub>2</sub> nanocomposites for antimicrobial coatings. *J Phys Chem B* 109(18):8889–8898. doi:10.1021/jp0502196
- Fujishima A, Honda K (1972) Electrochemical photolysis of water at a semiconductor electrode. *Nature* 238(5358):37–38
- Fujishima A, Zhang X (2006) Titanium dioxide photocatalysis: present situation and future approaches. *C R Chim* 9(5–6):750–760
- Fujishima A, Hashimoto K, Watanabe T (1997) Photocatalysis: fundamentals and applications. Tokyo CMC Co. Ltd. (English translation 1999, Tokyo, BMC Inc.)
- Fujishima A, Rao TN, Tryk DA (2000) Titanium dioxide photocatalysis. *J Photochem Photobiol C* 1(1):1–21
- Fujishima A, Zhang X, Tryk DA (2008) TiO<sub>2</sub> photocatalysis and related surface phenomena. *Surf Sci Rep* 63(12):515–582
- Gage JP, Roberts TM, Duffy JE (2005) Susceptibility of *Pseudomonas aeruginosa* biofilm to UV-A illumination over photocatalytic and non-photocatalytic surfaces. *Biofilms* 2(3):155–163
- Gamage J, Zhang Z (2010) Applications of photocatalytic disinfection. *Int J Photoen* 2010, Article ID 764870, 11 pp
- Gartner M, Anastasescu C, Zaharescu M, Enache M, Dumitru L, Stoica T, Stoica TF, Trapalis C (2009) The simulation in the real conditions of antibacterial activity of TiO<sub>2</sub> (Fe) films with optimized morphology. *Nanostruct Mater Nanotechnol* 29(8):67–76
- Geng X, Filipe C, Pelton R (2008) Antibacterial paper from photocatalytic TiO<sub>2</sub>. *Appita J* 61(6):456–460
- Gerrity D, Ryu H, Crittenden J, Abbaszadegan M (2008) Photocatalytic inactivation of viruses using titanium dioxide nanoparticles and low-pressure UV light. *J Environ Sci Health A* 43(11):1261–1270
- Giannantonio DJ, Kurth JC, Kurtis KE, Sobecky PA (2009) Effects of concrete properties and nutrients on fungal colonization and fouling. *Int Biodeterior Biodegrad* 63(3):252–259. doi:10.1016/j.ibiod.2008.10.002
- Gogniat G, Dukan S (2007) TiO<sub>2</sub> photocatalysis causes DNA damage via Fenton reaction-generated hydroxyl radicals during the recovery period. *Appl Environ Microbiol* 73(23):7740–7743. doi:10.1128/aem.01079-07
- Gogniat G, Thyssen M, Denis M, Pulgarin C, Dukan S (2006) The bactericidal effect of TiO<sub>2</sub> photocatalysis involves adsorption onto catalyst and the loss of membrane integrity. *FEMS Microbiol Lett* 258(1):18–24. doi:10.1111/j.1574-6968.2006.00190.x
- Goswami DY, Trivedi DM, Block SS (1997) Photocatalytic disinfection of indoor air. *Trans Am Soc Mech Eng* 119:92–96
- Goswami TK, Hingorani SK, Greist HT, Goswami DY, Block SS (1999) Photocatalytic system to destroy bioaerosols in air. *J Adv Oxid Technol* 4:185–188
- Greist HT, Hingorani, SK, Kelly K, Goswami DY (2002) Using scanning electron microscopy to visualize photocatalytic mineralization of airborne microorganisms. Proceedings of the 9th International Conference on Indoor Air Quality and Climate, July 2002, Monterey, California, pp 712–717
- Guillard C, Bui TH, Felix C, Moules V, Lina B, Lejeune P (2008) Microbiological disinfection of water and air by photocatalysis. *C R Chim* 11(1–2):107–113. doi:10.1016/j.crci.2007.06.007
- Guimaraes JR, Barretto AS (2003) Photocatalytic inactivation of *Clostridium perfringens* and coliphages in water. *Braz J Chem Eng* 20(4):403–411
- Gumy D, Morais C, Bowen P, Pulgarin C, Giraldo S, Hadju R, Kiwi J (2006a) Catalytic activity of commercial TiO<sub>2</sub> powders for the abatement of the bacteria (*E. coli*) under solar simulated light: influence of the isoelectric point. *Appl Catal B* 63:76–84. doi:10.1016/j.apcatb.2005.09.013
- Gumy D, Rincon AG, Hajdu R, Pulgarin C (2006b) Solar photocatalysis for detoxification and disinfection of water: different types of suspended and fixed TiO<sub>2</sub> catalysts study. *Sol Energy* 80(10):1376–1381. doi:10.1016/j.solener.2005.04.026
- Guo S, Wu Z, Zhao W (2009) TiO<sub>2</sub>-based building materials: above and beyond traditional applications. *Chin Sci Bull* 54(7):1137–1142
- Gupta KK, Jassal M, Agrawal AK (2008) Sol-gel derived titanium dioxide finishing of cotton fabric for self cleaning. *Ind J Fibre Text Res* 33(4):443–450
- Han W, Zhang PH, Cao WC, Yang DL, Taira S, Okamoto Y, Arai JL, Yan XY (2004) The inactivation effect of photocatalytic titanium apatite filter on SARS virus. *Prog Biochem Biophys* 31(11):982–985
- Hara-Kudo Y, Segawa Y, Kimura K (2006) Sanitation of seawater effluent from seaweed processing plants using a photo-catalytic TiO<sub>2</sub> oxidation. *Chemosphere* 62(1):149–154
- Harper JC, Christensen PA, Egerton TA (2000) Effect of catalyst type on the kinetics of photoelectrical disinfection of water inoculated with *E. coli*. *J Appl Electrochem* 31:623–628
- Hashimoto K, Irie H, Fujishima A (2005) TiO<sub>2</sub> photocatalysis: a historical overview and future prospects. *Jap J Appl Phys Pt 1* 44(12):8269–8285
- He C, Yu Y, Hu X, Larbot A (2002) Influence of silver doping on the photocatalytic activity of titania films. *Appl Surf Sci* 200:239–247
- Herrera Melián JA, Doña Rodríguez JM, Viera Suárez A, Tello Rondón E, Valdés Do Campo C, Arana J, Pérez Peña J (2000) The photocatalytic disinfection of urban waste waters. *Chemosphere* 41(3):323–327
- Hirakawa T, Kamat PV (2005) Charge separation and catalytic activity of Ag–TiO<sub>2</sub> core-shell composite clusters under UV irradiation. *J Am Chem Soc* 127(11):3928–3934
- Hirakawa K, Mori M, Yoshida M, Oikawa S, Kawanishi S (2004) Photo-irradiated titanium dioxide catalyzes site specific DNA damage via generation of hydrogen peroxide. *Free Radic Res* 38(5):439–447. doi:10.1080/1071576042000206487
- Honda H, Ishizaki A, Soma R, Hashimoto K, Fujishima A (1998) Application of photocatalytic reactions caused by TiO<sub>2</sub> film to

- improve the maintenance factor of lighting systems. *J Illum Eng Soc* 27(1):42–47
- Hong J, Ma H, Otaki M (2005) Controlling algal growth in photo-dependent decolorant sludge by photocatalysis. *J Biosci Bioeng* 6:592–597
- Horie Y, David DA, Taya M, Tone S (1996a) Effects of light intensity and titanium dioxide concentration on photocatalytic sterilization rates of microbial cells. *Ind Eng Chem Res* 35(11):3920–3926
- Horie Y, Taya M, Tone S (1996b) Photocatalytic sterilization of microbial cells with titania thin film prepared by sol–gel method. *Kagaku Kogaku Ronbunshu* 22(5):1244–1245
- Horie Y, Taya M, Tone S (1998) Effect of cell adsorption on photosterilization of *Escherichia coli* over titanium dioxide-activated charcoal granules. *J Chem Eng Jpn* 31(6):922–929
- Hu C, Lan Y, Qu J, Hu X, Wang A (2006) Ag/AgBr/TiO<sub>2</sub> visible light photocatalyst for destruction of azodyes and bacteria. *J Phys Chem B* 110(9):4066–4072
- Hu C, Guo J, Qu J, Hu X (2007) Photocatalytic degradation of pathogenic bacteria with AgI/TiO<sub>2</sub> under visible light irradiation. *Langmuir* 23(9):4982–4987
- Huang Z, Maness PC, Blake DM, Wolfrum EJ, Smolinski SL, Jacoby WA (2000) Bactericidal mode of titanium dioxide photocatalysis. *J Photochem Photobiol A* 130(2–3):163–170
- Hur JS, Oh SO, Lim KM, Jung JS, Kim JW, Koh YJ (2005) Novel effects of TiO<sub>2</sub> photocatalytic ozonation on control of postharvest fungal spoilage of kiwifruit. *Postharvest Biol Technol* 35(1):109–113
- Ibáñez JA, Litter MI, Pizarro RA (2003) Photocatalytic bactericidal effect of TiO<sub>2</sub> on *Enterobacter cloacae*. Comparative study with other Gram (–) bacteria. *J Photochem Photobiol A* 157(1):81–85
- Imlay JA, Fridovich I (1992) Suppression of oxidative envelope damage by pseudoreversion of a superoxide dismutase-deficient mutant of *Escherichia coli*. *J Bacteriol* 174(3):953–961
- Ireland JC, Klostermann P, Rice EW, Clark RM (1993) Inactivation of *Escherichia coli* by titanium dioxide photocatalytic oxidation. *Appl Environ Microbiol* 59(5):1668–1670
- Jacobsen AE (1949) Titanium dioxide pigments—correlation between photochemical reactivity and chalking. *Ind Eng Chem* 41(3):523–526
- Jacoby WA, Maness PC, Wolfrum EJ, Blake DM, Fennell JA (1998) Mineralization of bacterial cell mass on a photocatalytic surface in air. *Environ Sci Technol* 32(17):2650–2653
- Jucker BA, Harms H, Hug SJ, Zehnder AJB (1997) Adsorption of bacterial surface polysaccharides on mineral oxides is mediated by hydrogen bonds. *Colloids Surf B* 9(6):331–343
- Kakita Y, Kashige N, Miake F, Watanabe K (1997) Photocatalysis-dependent inactivation of *Lactobacillus* phage PL-1 by a ceramics preparation. *Biosci Biotechnol Biochem* 61(11):1947–1948
- Kakita Y, Obuchi E, Nakano K, Murata K, Kuroiwa A, Miake F, Watanabe K (2000) Photocatalytic inactivation of *Lactobacillus* PL-1 phages by a thin film of titania. *Biocontrol Sci* 5(2):73–79
- Kambala VSR, Naidu R (2009) Disinfection studies on TiO<sub>2</sub> thin films prepared by a sol–gel method. *J Biomed Nanotechnol* 5(1):121–129. doi:10.1166/jbn.2009.1002
- Kangwansupamonkon W, Lauruengtana V, Surassmo S, Ruktanonchai U (2009) Antibacterial effect of apatite-coated titanium dioxide for textiles applications. *Nanomed Nanotechnol Biol Med* 5:240–249
- Kashige N, Kakita Y, Nakashima Y, Miake F, Watanabe K (2001) Mechanism of the photocatalytic inactivation of *Lactobacillus casei* phage PL-1 by titania thin film. *Curr Microbiol* 42(3):184–189
- Kashyout AB, Soliman M, El-Haleem DA (2006) Disinfection of bacterial suspensions by photocatalytic oxidation using TiO<sub>2</sub> nanoparticles under ultraviolet illumination. *AEJ - Alexandria Eng J* 45(3):367–371
- Kato T, Tohma H, Miki O, Shibata T, Tamura M (2005) Degradation of norovirus in sewage treatment water by photocatalytic ultraviolet disinfection. *Nippon Steel Tech Rep* 92:41–44
- Kerstens I, De Keyser T, Verstraete W (1998) Sensitivity of bacteria to photoactivated titanium dioxide in comparison with UV irradiation. *Ind J Eng Mater Sci* 5(4):211–216
- Khan U, Benabderrazik N, Bourdelais AJ, Baden DG, Rein K, Gardinali PR, Arroyo L, O’Shea KE (2010) UV and solar TiO<sub>2</sub> photocatalysis of brevetoxins (pbtxs). *Toxicol* 55(5):1008–1016
- Kikuchi Y, Sunada K, Iyoda T, Hashimoto K, Fujishima A (1997) Photocatalytic bactericidal effect of TiO<sub>2</sub> thin films: dynamic view of the active oxygen species responsible for the effect. *J Photochem Photobiol A* 106(1–3):51–56
- Kim SC, Lee DK (2005) Inactivation of algal blooms in eutrophic water of drinking water supplies with the photocatalysis of TiO<sub>2</sub> thin film on hollow glass beads. *Wat Sci Technol* 52(9):145–152
- Kim B, Kim D, Cho D, Cho S (2003) Bactericidal effect of TiO<sub>2</sub> photocatalyst on selected food-borne pathogenic bacteria. *Chemosphere* 52(1):277–281. doi:10.1016/s0045-6535(03)00051-1
- Kim SY, Nishioka M, Taya M (2004) Promoted proliferation of an SOD-deficient mutant of *Escherichia coli* under oxidative stress induced by photoexcited TiO<sub>2</sub>. *FEMS Microbiol Lett* 236(1):109–114
- Kiwi J, Nadtochenko V (2004) New evidence for TiO<sub>2</sub> photocatalysis during bilayer lipid peroxidation. *J Phys Chem B* 108(45):17675–17684. doi:10.1021/jp048281a
- Kiwi J, Nadtochenko V (2005) Evidence for the mechanism of photocatalytic degradation of the bacterial wall membrane at the TiO<sub>2</sub> interface by ATR-FTIR and laser kinetic spectroscopy. *Langmuir* 21(10):4631–4641. doi:10.1021/la0469831
- Koide S, Nonami T (2007) Disinfecting efficacy of a plastic container covered with photocatalyst for postharvest. *Food Control* 18(1):1–4. doi:10.1016/j.foodcont.2005.08.001
- Koizumi Y, Taya M (2002a) Photocatalytic inactivation rate of phage MS2 in titanium dioxide suspensions containing various ionic species. *Biotechnol Lett* 24(6):459–462
- Koizumi Y, Taya M (2002b) Kinetic evaluation of biocidal activity of titanium dioxide against phage MS2 considering interaction between the phage and photocatalyst particles. *Biochem Eng J* 12(2):107–116
- Koizumi Y, Yamada R, Nishioka M, Matsumura Y, Tsuchido T, Taya M (2002) Deactivation kinetics of *Escherichia coli* cells correlated with intracellular superoxide dismutase activity in photoreaction with titanium dioxide particles. *J Chem Technol Biotechnol* 77(6):671–677
- Kozlova EA, Safatov AS, Kiselev SA, Marchenko VY, Sergeev AA, Skarnovich MO, Emelyanova EK, Smetannikova MA, Buryak GA, Vorontsov AV (2010) Inactivation and mineralization of aerosol deposited model pathogenic microorganisms over TiO<sub>2</sub> and Pt/TiO<sub>2</sub>. *Environ Sci Technol* 44(13):5121–5126
- Kubacka A, Cerrada ML, Serran C, Fernandez-Garcia M, Ferrer M (2008a) Light-driven novel properties of TiO<sub>2</sub>-modified polypropylene-based nanocomposite films. *J Nanosci Nanotechnol* 8(6):3241–3246. doi:10.1166/jnn.2008.363
- Kubacka A, Ferrer M, Martínez-Arias A, Fernández-García M (2008b) Ag promotion of TiO<sub>2</sub>-anatase disinfection capability: study of *Escherichia coli* inactivation. *Appl Catal B* 84(1–2):87–93
- Kühn KP, Chaberny IF, Massholder K, Stickler M, Benz VW, Sonntag HG, Erdinger L (2003) Disinfection of surfaces by photocatalytic oxidation with titanium dioxide and UVA light. *Chemosphere* 53(1):71–77
- Lan Y, Hu C, Hu X, Qu J (2007) Efficient destruction of pathogenic bacteria with AgBr/TiO<sub>2</sub> under visible light irradiation. *Appl Catal B* 73(3):354–360
- Laot N, Narkis N, Neeman I, Bilanovic D, Armon R (1999) TiO<sub>2</sub> photocatalytic inactivation of selected microorganisms under

- various conditions: sunlight, intermittent and variable irradiation intensity, CdS augmentation and entrapment of TiO<sub>2</sub> into sol–gel. *J Adv Oxid Technol* 4:97–102
- Lawton LA, Robertson PKJ, Cornish BJA, Jaspars M (1999) Detoxification of microcystins (cyanobacterial hepatotoxins) using TiO<sub>2</sub> photocatalytic oxidation. *Environ Sci Technol* 33(5):771–775
- Lawton LA, Robertson PKJ, Cornish BJA, Marr IL, Jaspars M (2003) Processes influencing surface interaction and photocatalytic destruction of microcystins on titanium dioxide photocatalysts. *J Catal* 213(1):109–113
- Lee S, Nishida K, Otaki M, Ohgaki S (1997) Photocatalytic inactivation of phage Q $\beta$  By immobilized titanium dioxide mediated photocatalyst. *Wat Sci Technol* 35:101–106
- Lee JH, Kang M, Choung S-J, Ogino K, Kim MS, M-S PK-Y, Kim J-B (2004) The preparation of TiO<sub>2</sub> nanometer photocatalyst film by a hydrothermal method and its sterilization performance for *Giardia lamblia*. *Wat Res* 38:713–719
- Li C-CT, Lai H-H, Chan C-W (2003) Ultraviolet germicidal irradiation and titanium dioxide photocatalyst for controlling *Legionella pneumophila*. *Aerosol Sci Technol* 37:961–966
- Li Y, Leung P, Yao L, Song QW, Newton E (2006) Antimicrobial effect of surgical masks coated with nanoparticles. *J Hosp Infect* 62(1):58–63
- Li Y, Ma M, Wang X (2008) Inactivated properties of activated carbon-supported TiO<sub>2</sub> nanoparticles for bacteria and kinetic study. *J Environ Sci* 20(12):1527–1533
- Lin CY, Li CS (2003a) Effectiveness of titanium dioxide photocatalyst filters for controlling bioaerosols. *Aerosol Sci Technol* 37(2):162–170. doi:10.1080/02786820390112623
- Lin CY, Li CS (2003b) Inactivation of microorganisms on the photocatalytic surfaces in air. *Aerosol Sci Technol* 37(12):939–946. doi:10.1080/02786820390230352
- Lin ZX, Li ZH, Wang XX, Fu XZ, Yang GQ, Lin HX, Meng C (2006) Inactivation efficiency of TiO<sub>2</sub> on H1N1 influenza virus. *Gaodeng Xuexiao Huaxue Xuebao Chem J Chin Univ* 27(4):721–725
- Linkous CA, Carter GJ, Locuson DV, Ouellette AJ, Slattery DK, Smith LA (2000) Photocatalytic inhibition of algae growth using TiO<sub>2</sub>, WO<sub>3</sub>, and cocatalyst modifications. *Environ Sci Technol* 34(22):4754–4758
- Liu HL, Yang TCK (2003) Photocatalytic inactivation of *Escherichia coli* and *Lactobacillus helveticus* by ZnO and TiO<sub>2</sub> activated with ultraviolet light. *Proc Biochem* 39(4):475–481. doi:10.1016/S0032-9592(03)00084-0
- Liu I, Lawton LA, Bahnemann DW, Robertson PKJ (2005) The photocatalytic destruction of the cyanotoxin, nodularin using TiO<sub>2</sub>. *Appl Catal B* 60(3–4):245–252
- Liu Y, Li J, Qiu X, Burda C (2007a) Bactericidal activity of nitrogen-doped metal oxide nanocatalysts and the influence of bacterial extracellular polymeric substances (EPS). *J Photochem Photobiol A* 190(1):94–100
- Liu HR, Lin Y, Ye RF, Song L, Chen Q (2007b) Structure and antibacterial properties of Ag-doped TiO<sub>2</sub> porous materials. *Bio-ceramics 19* published in *Key Eng Mater* 330–332(II):995–998
- Liu L-f, John B, Yeung KL, Si G (2007c) Non-UV based germicidal activity of metal-doped TiO<sub>2</sub> coating on solid surfaces. *J Environ Sci* 19(6):745–750
- Lonnen J, Kilvington S, Kehoe SC, Al-Touati F, McGuigan KG (2005) Solar and photocatalytic disinfection of protozoan, fungal and bacterial microbes in drinking water. *Wat Res* 39(5):877–883. doi:10.1016/j.watres.2004.11.023
- Lu JW, Li FB, Guo T, Lin LW, Hou MF, Liu TX (2006) TiO<sub>2</sub> photocatalytic antifungal technique for crops diseases control. *J Environ Sci Chin* 18(2):397–401
- Luo L, Miao L, Tanemura S, Tanemura M (2008) Photocatalytic sterilization of TiO<sub>2</sub> films coated on Al fiber. *Mater Sci Eng B* 148(1–3):183–186
- Makowski A, Wardas W (2001) Photocatalytic degradation of toxins secreted to water by cyanobacteria and unicellular algae and photocatalytic degradation of the cells of selected microorganisms. *Curr Top Biophys* 251:19–25
- Maneerat C, Hayata Y (2006) Antifungal activity of TiO<sub>2</sub> photocatalysis against *Penicillium expansum* in vitro and in fruit tests. *Int J Food Microbiol* 107(2):99–103. doi:10.1016/j.ijfoodmicro.2005.08.018
- Maness PC, Smolinski S, Blake DM, Huang Z, Wolfgram EJ, Jacoby WA (1999) Bactericidal activity of photocatalytic TiO<sub>2</sub> reaction: toward an understanding of its killing mechanism. *Appl Environ Microbiol* 65(9):4094–4098
- Marugan J, van Grieken R, Pablos C, Sordo C (2006) Analogies and differences between photocatalytic oxidation of chemicals and photocatalytic inactivation of microorganisms. *Wat Res* 44(3):789–796
- Marugan J, van Grieken R, Sordo C, Cruz C (2008) Kinetics of the photocatalytic disinfection of *Escherichia coli* suspensions. *Appl Catal B* 82(1–2):27–36
- Matusunga T (1985) Sterilization with particulate photoconductor. *J Antibact Antifung Agents* 13:211–220
- Matsunaga T, Tomoda R, Nakajima T, Wake H (1985) Photoelectrochemical sterilization of microbial cells by semiconductor powders. *FEMS Microbiol Lett* 29(1–2):211–214
- Matsunaga T, Tomoda R, Nakajima T, Nakamura N, Komine T (1988) Continuous-sterilization system that uses photoconductor powders. *Appl Environ Microbiol* 54(6):1330–1333
- Matsunaga T, Okochi M, Nakasono S (1995) Direct count of bacteria using fluorescent dyes: application to assessment of electrochemical disinfection. *Anal Chem* 67(24):4487–4490
- McCullagh C, Robertson JMC, Bahnemann DW, Robertson PKJ (2007) The application of TiO<sub>2</sub> photocatalysis for disinfection of water contaminated with pathogenic micro-organisms: a review. *Res Chem Intermed* 33(3–5):359–375
- McLoughlin OA, Fernández Ibáñez P, Gernjak W, Malato Rodriguez S, Gill LW (2004a) Photocatalytic disinfection of water using low cost compound parabolic collectors. *Sol Energy* 77(5):625–633
- McLoughlin OA, Kehoe SC, McGuigan KG, Duffy EF, Al Touati F, Gernjak W, Oller Alberola I, Malato Rodriguez S, Gill LW (2004b) Solar disinfection of contaminated water: a comparison of three small-scale reactors. *Sol Energy* 77(5):657–664
- Mills A, Le Hunte S (1997) An overview of semiconductor photocatalysis. *J Photochem Photobiol A* 108(1):1–35
- Miron C, Roca A, Hoisie S, Cozorici P, Sirghi L (2005) Photoinduced bactericidal activity of TiO<sub>2</sub> thin films obtained by radio-frequency magnetron sputtering deposition. *J Optoelectron Adv Mater* 7(2):915–919
- Miyagi T, Kamei M, Mitsunashi T, Ishigaki T, Yamazaki A (2004) Charge separation at the rutile/anatase interface: a dominant factor of photocatalytic activity. *Chem Phys Lett* 390(4–6):399–402
- Mo AC, Xu W, Xian S, Li Y, Bai S (2007) Antibacterial activity of silver–hydroxyapatite/titania nanocomposite coating on titanium against oral bacteria. *Bio-ceramics 19* published in *Key Eng Mater* 330–332:455–458
- Muraleedharan P, Gopal J, George RP, Khatak HS (2003) Photocatalytic bactericidal property of anodized Ti6Al4V alloy. *Curr Sci* 84(2):197–199
- Musil J, Louda M, Cerstvy R, Baroch P, Ditta IB, Steele A, Foster HA (2009) Two-functional direct current sputtered silver-containing titanium dioxide thin films. *Nanoscale Res Lett* 4(4):313–320. doi:10.1007/s11671-008-9244-z
- Muszkat L, Feigelson L, Bir L, Muszkat KA, Teitel M, Dornay I, Kirchner B, Kritzman G (2005) Solar photo-inactivation of phytopathogens by trace level hydrogen peroxide and titanium dioxide photocatalysis. *Phytoparasitica* 33(3):267–274

- Nadtochenko VA, Rincon AG, Stanca SE, Kiwi J (2005) Dynamics of *E. coli* membrane cell peroxidation during TiO<sub>2</sub> photocatalysis studied by ATR-FTIR spectroscopy and AFM microscopy. *J Photochem Photobiol A* 169(2):131–137
- Nadtochenko V, Denisov N, Sarkisov O, Gumy D, Pulgarin C, Kiwi J (2006) Laser kinetic spectroscopy of the interfacial charge transfer between membrane cell walls of *E. coli* and TiO<sub>2</sub>. *J Photochem Photobiol A* 181(2–3):401–407
- Nadtochenko VA, Sarkisov OM, Nikandrov VV, Chubukov PA, Denisov NN (2008) Inactivation of pathogenic microorganisms in the photocatalytic process on nanosized TiO<sub>2</sub> crystals. *Russ J Phys Chem B* 2(1):105–114. doi:10.1007/s11826-008-1016-0
- Nagame S, Oku T, Kambara M, Konishi K (1989) Antibacterial effect of the powdered semiconductor TiO<sub>2</sub> on the viability of oral microorganisms. *J Dent Res* 68(Special issue):1697–1698
- Nakamura H, Tanaka M, Shinohara S, Gotoh M, Karube I (2007) Development of a self-sterilizing lancet coated with a titanium dioxide photocatalytic nano-layer for self-monitoring of blood glucose. *Biosens Bioelectron* 22(9–10):1920–1925
- Navalon S, Alvaro M, Garcia H, Escrig D, Costa V (2009) Photocatalytic water disinfection of *Cryptosporidium parvum* and *Giardia lamblia* using a fibrous ceramic TiO<sub>2</sub> photocatalyst. *Wat Sci Technol* 59:639–645
- Nimitrakoolchai OU, Supothina S (2008) Nanocrystalline TiO<sub>2</sub> coated-fabric for UV shielding and anti-bacterial functions. *Mater Sci Forum* 2008:21–24
- Ogino C, Farshbaf Dadjour M, Takaki K, Shimizu N (2006) Enhancement of sonocatalytic cell lysis of *Escherichia coli* in the presence of TiO<sub>2</sub>. *Biochem Eng J* 32(2):100–105
- Ohko Y, Utsumi Y, Niwa C, Tatsuma T, Kobayakawa K, Satoh Y, Kubota Y, Fujishima A (2001) Self-sterilizing and self-cleaning of silicone catheters coated with TiO<sub>2</sub> photocatalyst thin films: a preclinical work. *J Biomed Mater Res* 58(1):97–101
- Olive PL, Bonath JP, Durand RE (1990) Heterogenicity in radiation induced DNA damage and repair in tumor and normal cells. *Radiat Res* 112:86–94
- Oka Y, Kim WC, Yoshida T, Hirashima T, Mouri H, Urade H, Itoh Y, Kubo T (2008) Efficacy of titanium dioxide photocatalyst for inhibition of bacterial colonization on percutaneous implants. *J Biomed Mater Res B* 86(2):530–540
- Ortiz López JE, Jacoby WA (2002) Microfibrous mesh coated with titanium dioxide: a self-sterilizing, self-cleaning filter. *J Air Waste Manage Assoc* 52(10):1206–1213
- Otaki M, Hirata T, Ohgaki S (2000) Aqueous microorganisms inactivation by photocatalytic reaction. *Wat Sci Technol* 42(3–4):103–108
- Pal A, Mint X, Yu LE, Pehkonen SO, Ray MB (2005) Photocatalytic inactivation of bioaerosols by TiO<sub>2</sub> coated membrane. *Int J Chem React Eng* 3:14p
- Pal A, Pehkonen SO, Yu LE, Ray MB (2007) Photocatalytic inactivation of Gram-positive and Gram-negative bacteria using fluorescent light. *J Photochem Photobiol A* 186(2–3):335–341. doi:10.1016/j.jphotochem.2006.09.002
- Pal A, Pehkonen SO, Yu LE, Ray MB (2008) Photocatalytic inactivation of airborne bacteria in a continuous-flow reactor. *Ind Eng Chem Res* 47(20):7580–7585. doi:10.1021/ie701739g
- Paschoalino MP, Jardim WF (2008) Indoor air disinfection using a polyester supported TiO<sub>2</sub> photo-reactor. *Indoor Air* 18(6):473–479. doi:10.1111/j.1600-0668.2008.00548.x
- Paspaltsis I, Kotta K, Lagoudaki R, Grigoriadis N, Poullos I, Sklaviadis T (2006) Titanium dioxide photocatalytic inactivation of prions. *J Gen Virol* 87(10):3125–3130
- Peller JR, Whitman RL, Griffith S, Harris P, Peller C, Scalzitti J (2007) TiO<sub>2</sub> as a photocatalyst for control of the aquatic invasive alga, *Cladophora*, under natural and artificial light. *J Photochem Photobiol A* 186(2–3):212–217
- Peng L, Wenli D, Qisui W, Xi L (2010) The envelope damage of *Tetrahymena* in the presence of TiO<sub>2</sub> combined with UV light. *Photochem Photobiol* 86(3):633–638
- Pham HN, McDowell T, Wilkins E (1995) Photocatalytically-mediated disinfection of water using TiO<sub>2</sub> as a catalyst and spore-forming *Bacillus pumilus* as a model. *J Environ Sci Health A* 30(3):627–636
- Pham HN, Wilkins E, Heger KS, Kauffman D (1997) Quantitative analysis of variations in initial *Bacillus pumilus* spore densities in aqueous TiO<sub>2</sub> suspension and design of a photocatalytic reactor. *J Environ Sci Health A* 32(1):153–163
- Poulios I, Spathis P, Grigoriadou A, Delidou K, Tsoumparis P (1999) Protection of marbles against corrosion and microbial corrosion with TiO<sub>2</sub> coatings. *J Environ Sci Health A* 34(7):1455–1471
- Pratap Reddy M, Phil HH, Subrahmanyam M (2008) Photocatalytic disinfection of *Escherichia coli* over titanium(IV) oxide supported on Zeolite. *Catal Lett* 123(1–2):56–64
- Pryor WA (1986) Oxy-radicals and related species: their formation, lifetimes and reactions. *Ann Rev Physiol* 48:657–663
- Quisenberry LR, Loetscher LH, Boyd JE (2009) Catalytic inactivation of bacteria using Pd-modified titania. *Cat Commun* 10(10):1417–1422
- Renz C (1921) Lichtreaktionen der Oxyde des Titans, Cers und der Erdsäuren. *Helv Chim Acta* 4:961–968. doi:10.1002/hlca.192100401101
- Rincon AG, Pulgarin C (2003) Photocatalytic inactivation of *E. coli*: effect of (continuous-intermittent) light intensity and of (suspended-fixed) TiO<sub>2</sub> concentration. *Appl Catal B* 44(3):263–284. doi:10.1016/s0926-3373(03)00076-6
- Rincón AG, Pulgarin C (2004a) Bactericidal action of illuminated TiO<sub>2</sub> on pure *Escherichia coli* and natural bacterial consortia: post-irradiation events in the dark and assessment of the effective disinfection time. *Appl Catal B* 49(2):99–112
- Rincón AG, Pulgarin C (2004b) Effect of pH, inorganic ions, organic matter and H<sub>2</sub>O<sub>2</sub> on *E. coli* K12 photocatalytic inactivation by TiO<sub>2</sub>: implications in solar water disinfection. *Appl Catal B* 51(4):283–302
- Rincón AG, Pulgarin C (2005) Use of coaxial photocatalytic reactor (caphore) in the TiO<sub>2</sub> photo-assisted treatment of mixed *E. coli* and *Bacillus* sp. and bacterial community present in wastewater. *Catal Today* 101(3–4 SPEC. ISS):331–344
- Rincón AG, Pulgarin C (2007) Solar photolytic and photocatalytic disinfection of water at laboratory and field scale. Effect of the chemical composition of water and study of the postirradiation events. *J Sol Energy Eng Trans ASME* 129(1):100–110
- Robertson JMC, Robertson PKJ, Lawton LA (2005) A comparison of the effectiveness of TiO<sub>2</sub> photocatalysis and UVA photolysis for the destruction of three pathogenic micro-organisms. *J Photochem Photobiol A* 175(1):51–56. doi:10.1016/j.jphotochem.2005.04.033
- Rodriguez J, Jorge C, Ziolla P, Palomino J, Zanabria P, Ponce S, Solas JL, Estrada W (2007) Solar water disinfection studies with supported TiO<sub>2</sub> and polymer-supported R(II) sensitizer in a compound parabolic collector. *J Sol Energy Eng Trans ASME* 132(1):0110011–0110015
- Rodriguez-Gonzalez V, Alfaro SO, Torres-Martanez LM, Cho SH, Lee SW (2010) Silver–TiO<sub>2</sub> nanocomposites: synthesis and harmful algae bloom UV-photoelimination. *Appl Catal B* 98(3–4):229–234
- Ryu H, Gerrity D, Crittenden JC, Abbaszadegan M (2008) Photocatalytic inactivation of *Cryptosporidium parvum* with TiO<sub>2</sub> and low-pressure ultraviolet irradiation. *Wat Res* 42(6–7):1523–1530. doi:10.1016/j.watres.2007.10.037
- Saito T, Iwase T, Horie J, Morioka T (1992) Mode of photocatalytic bactericidal action of powdered semiconductor TiO<sub>2</sub> on mutants streptococci. *J Photochem Photobiol B* 14(4):369–379

- Salih FM (2002) Enhancement of solar inactivation of *Escherichia coli* by titanium dioxide photocatalytic oxidation. *J Appl Microbiol* 92(5):920–926
- Salih FM (2004) Water purification by a combination of sunlight, titanium dioxide and alum. *Proceedings of the 2004 World Water and Environmental Resources Congress: Critical Transitions in Water and Environment Resources Management*, pp 2918–2926
- Sato T, Taya M (2006a) Enhancement of phage inactivation using photocatalytic titanium dioxide particles with different crystalline structures. *Biochem Eng J* 28(3):303–308
- Sato T, Taya M (2006b) Kinetic consideration of the effect of organic impurities on photocatalytic phage inactivation with TiO<sub>2</sub>. *Kagaku Kogaku Ronbunshu* 32(3):288–292
- Sato T, Taya M (2006c) Copper-aided photo sterilization of microbial cells on TiO<sub>2</sub> film under irradiation from a white light fluorescent lamp. *Biochem Eng J* 30(2):199–204. doi:10.1016/j.bej.2006.04.002
- Sato T, Koizumi Y, Taya M (2003) Photocatalytic deactivation of airborne microbial cells on TiO<sub>2</sub>-loaded plate. *Biochem Eng J* 14(2):149–152
- Sawada D, Ohmasa M, Fukuda M, Masuno K, Koide H, Tsunoda S, Nakamura K (2005) Disinfection of some pathogens of mushroom cultivation by photocatalytic treatment. *Mycosci* 46(1):54–60
- Selma MV, Allende A, Lopez-Galvez F, Conesa MA, Gil MI (2008) Heterogeneous photocatalytic disinfection of wash waters from the fresh-cut vegetable industry. *J Food Prot* 71(2):286–292
- Senogles P-J, Scott JA, Shaw G (2000) Efficiency of UV treatment with and without the photocatalyst titanium dioxide for the degradation of the cyanotoxin cylindrospermopsin. *Res Environ Biotechnol* 3(2–3):111–125
- Senogles P-J, Scott JA, Shaw G, Stratton H (2001) Photocatalytic degradation of the cyanotoxin cylindrospermopsin, using titanium dioxide and UV irradiation. *Wat Res* 35(5):1245–1255
- Shah RR, Kaewgun S, Lee BI, Tzeng TRJ (2008) The antibacterial effects of biphasic brookite–anatase titanium dioxide nanoparticles on multiple-drug-resistant *Staphylococcus aureus*. *J Biomed Nanotechnol* 4(3):339–348. doi:10.1166/jbn.2008.324
- Sheel DW, Brook LA, Ditta IB, Evans P, Foster HA, Steele A, Yates HM (2008) Biocidal silver and silver/titania composite films grown by chemical vapour deposition. *Int J Photoenergy*. Article ID 168185, 11 pp. doi:10.1155/2008/168185
- Shen XC, Zhang ZL, Zhou B, Peng J, Xie M, Zhang DW (2008) Visible light-induced plasmid DNA damage catalyzed by a CdSe/ZnS-photosensitized nano-TiO<sub>2</sub> film. *Environ Sci Technol* 42(14):5049–5054. doi:10.1021/es800668g
- Shephard GS, Stockenström S, De Villiers D, Engelbrecht WJ, Sydenham EW, Wessels GFS (1998) Photocatalytic degradation of cyanobacterial microcystin toxins in water. *Toxicon* 36(12):1895–1901
- Shieh KJ, Li M, Lee YH, Sheu SD, Liu YT, Wang YC (2006) Antibacterial performance of photocatalyst thin film fabricated by deflection effect in visible light. *Nanomed Nanotechnol Biol Med* 2(2):121–126
- Shiraishi F, Toyoda K, Fukinbara S, Obuchi E, Nakano K (1999) Photolytic and photocatalytic treatment of an aqueous solution containing microbial cells and organic compounds in an annular-flow reactor. *Chem Eng Sci* 54(10):1547–1552
- Sichel C, Blanco J, Malato S, Fernandez-Ibanez P (2007a) Effects of experimental conditions on *E. coli* survival during solar photocatalytic water disinfection. *J Photochem Photobiol A* 189(2–3):239–246. doi:10.1016/j.jphotochem.2007.02.004
- Sichel C, de Cara M, Tello J, Blanco J, Fernandez-Ibanez P (2007b) Solar photocatalytic disinfection of agricultural pathogenic fungi: *Fusarium* species. *Appl Catal B* 74(1–2):152–160. doi:10.1016/j.apcatb.2007.02.005
- Sichel C, Tello J, de Cara M, Fernandez-Ibanez P (2007c) Effect of UV solar intensity and dose on the photocatalytic disinfection of bacteria and fungi. *Catal Today* 129:152–160. doi:10.1016/j.cattod.2007.06.061
- Singh A, Singh R, Purohit S, Malodia P, Kumar R (2005) Photocatalytic disinfection of water using immobilized titanium dioxide. *Poll Res* 24(1):29–33
- Sjogren JC, Sierka RA (1994) Inactivation of phage MS2 by iron-aided titanium dioxide photocatalysis. *Appl Environ Microbiol* 60(1):344–347
- Skorb EV, Antonouskaya LI, Belyasova NA, Shchukin DG, Möhwald H, Sviridov DV (2008) Antibacterial activity of thin-film photocatalysts based on metal-modified TiO<sub>2</sub> and TiO<sub>2</sub>:In<sub>2</sub>O<sub>3</sub> nanocomposite. *Appl Catal B* 84(1–2):94–99
- Sökmen M, Candan F, Simer Z (2001) Disinfection of *E. coli* by the Ag–TiO<sub>2</sub>/UV system: lipidperoxidation. *J Photochem Photobiol A* 143(2–3):241–244
- Sökmen M, Degerli S, Aslan A (2008) Photocatalytic disinfection of *Giardia intestinalis* and *Acanthamoeba castellanii* cysts in water. *Exp Parasitol* 119(1):44–48
- Song SJ, Kim KS, Kim KH, Li HJ, Cho DL, Kim JB, Park HJ, Shon H, Kim JH (2008) Fabrication of TiO<sub>2</sub> impregnated stainless steel fiber photocatalysts and evaluation of photocatalytic activity. *J Korean Ind Eng Chem* 19(6):674–679
- Suketa N, Sawase T, Kitaura H, Naito M, Baba K, Nakayama K, Wennerberg A, Atsuta M (2005) An antibacterial surface on dental implants, based on the photocatalytic bactericidal effect. *Clin Implant Dent Relat Res* 7(2):105–111
- Sun DD, Tay JH, Tan KM (2003) Photocatalytic degradation of *E. coliform* in water. *Wat Res* 37(14):3452–3462. doi:10.1016/S0043-1354(03)00228-8
- Sunada K, Kikuchi Y, Hashimoto K, Fujishima A (1998) Bactericidal and detoxification effects of TiO<sub>2</sub> thin film photocatalysts. *Environ Sci Technol* 32(5):726–728
- Sunada K, Watanabe T, Hashimoto K (2003a) Bactericidal activity of copper-deposited TiO<sub>2</sub> thin film under weak UV light illumination. *Environ Sci Technol* 37(20):4785–4789. doi:10.1021/es034106g
- Sunada K, Watanabe T, Hashimoto K (2003b) Studies on photokilling of bacteria on TiO<sub>2</sub> thin film. *J Photochem Photobiol A* 156(1–3):227–233. doi:10.1016/S1010-6030(02)00434-3
- Suwalsky M, Schneider C, Mansilla HD, Kiwi J (2005) Evidence for the hydration effect at the semiconductor phospholipid-bilayer interface by TiO<sub>2</sub> photocatalysis. *J Photochem Photobiol B* 78(3):253–258
- Takashima H, Iida Y, Nakamura K, Kanno Y (2007) Microwave sterilization by TiO<sub>2</sub> filter coated with Ag thin film. *Conf Proc IEEE Int Conf Syst Man Cybernet* 2007:1413–1418
- Tatsuma T, Takeda S, Saitoh S, Ohko Y, Fujishima A (2003) Bactericidal effect of an energy storage TiO<sub>2</sub>–WO<sub>3</sub> photocatalyst in dark. *Electrochem Commun* 5(9):793–796. doi:10.1016/j.elcom.2003.07.003
- Tsuang YH, Sun JS, Huang YC, Lu CH, Chang WHS, Wang CC (2008) Studies of photokilling of bacteria using titanium dioxide nanoparticles. *Artific Organs* 32(2):167–174. doi:10.1111/j.1525-1594.2007.00530.x
- Ueda M, Sai H, Ikeda M, Ogawa M (2010) Formation of hydroxyapatite on titanium oxides in simulated body fluid under UV irradiation. *Mate Sci Forum* 654–656:2257–2260
- Vacaroiu C, Enache M, Gartner M, Popescu G, Anastasescu M, Brezeanu A, Todorova N, Giannakopoulou T, Trapalis C, Dumitru L (2009) The effect of thermal treatment on antibacterial properties of nanostructured TiO<sub>2</sub> (N) films illuminated with visible light. *World J Microbiol Biotechnol* 25(1):27–31
- Van Grieken R, Marugan J, Pablos C, Lopez A (2010) Comparison between the photocatalytic inactivation of Gram-positive *E.*

- faecalis* and Gram-negative *E. coli* faecal contamination indicator microorganisms. Appl Catal B 100:212–220
- Veselá M, Veselý M, Chomoucká J, Lipenská M (2008) Photocatalytic disinfection of water using Ag/TiO<sub>2</sub>. Chem Listy 102(15 SPEC. ISS):s507–s508
- Vidal A, Díaz AI, El Hraiki A, Romero M, Muguruza I, Senhaji F, González J (1999) Solar photocatalysis for detoxification and disinfection of contaminated water: pilot plant studies. Catal Today 54(2–3):283–290
- Vohra A, Goswami DY, Deshpande DA, Block SS (2006) Enhanced photocatalytic disinfection of indoor air. Appl Catal B 64(1–2):57–65. doi:10.1016/j.apcatb.2005.10.025
- Wamer WG, Yin JJ, Wei RR (1997) Oxidative damage to nucleic acids photosensitized by titanium dioxide. Free Radical Biol Med 23(6):851–858
- Wang Y, Yang X (2005) Photocatalytic effect on plasmid DNA damage under different UV irradiation time. Indoor Air 2005. Proc 10th Int Conf Indoor Air Qual Clim 1–5:2962–2965
- Wang Y, Yang X, Han Z (2005) Disinfection and bactericidal effect using photocatalytic oxidation. Trans Hong Kong Inst Eng 12(1):39–43
- Watts RJ, Kong S, Orr MP, Miller GC, Henry BE (1995) Photocatalytic inactivation of coliform bacteria and viruses in secondary wastewater effluent. Water Res 29(1):95–100
- Wei C, Lin WY, Zainal Z, Williams NE, Zhu K, Kruzic AP, Smith RL, Rajeshwar K (1994) Bactericidal activity of TiO<sub>2</sub> photocatalyst in aqueous media: toward a solar-assisted water disinfection system. Environ Sci Technol 28:934–938
- Wolfrum EJ, Huang J, Blake DM, Maness PC, Huang Z, Fiest J, Jacoby WA (2002) Photocatalytic oxidation of bacteria, bacterial and fungal spores, and model biofilm components to carbon dioxide on titanium dioxide-coated surfaces. Environ Sci Technol 36(15):3412–3419. doi:10.1021/es011423j
- Wu PG, Xie RC, Shang JK (2008) Enhanced visible-light photocatalytic disinfection of bacterial spores by palladium-modified nitrogen-doped titanium oxide. J Am Ceram Soc 9:2957–2962. doi:10.1111/j.1551-2916.2008.02573.x
- Wu D, Long M, Zhou J, Cai W, Zhu X, Chen C, Wu Y (2009a) Synthesis and characterization of self-cleaning cotton fabrics modified by TiO<sub>2</sub> through a facile approach. Surf Coat Technol 203(24):3728–3733
- Wu P, Xie R, Imlay JA, Shang JK (2009b) Visible-light-induced photocatalytic inactivation of bacteria by composite photocatalysts of palladium oxide and nitrogen-doped titanium oxide. Appl Catal B 88(3–4):576–581
- Wu B, Huang R, Sahu M, Feng X, Biswas P, Tang YJ (2010a) Bacterial responses to Cu-doped TiO<sub>2</sub> nanoparticles. Sci Total Environ 408(7):1755–1758
- Wu P, Imlay JA, Shang JK (2010b) Mechanism of *Escherichia coli* inactivation on palladium-modified nitrogen-doped titanium dioxide. Biomater 31(29):7526–7533
- Xiong B, Lei S, Gong W, Guo G, Zhang X (2006) Antibacterial kinetics of TiO<sub>2</sub>/montmorillonite photocatalyst. Huaxue Fanying Gongcheng Yu Gongyi/Chem React Eng Technol 22(6):507–512
- Yan G, Chen J, Hua Z (2009) Roles of H<sub>2</sub>O<sub>2</sub> and OH<sup>•</sup> in bactericidal action of immobilised TiO<sub>2</sub> thin film reactor: an ESR study. J Photochem Photobiol A 207:153–159
- Yang X, Wang Y (2008) Photocatalytic effect on plasmid DNA damage under different UV irradiation time. Build Environ 43(3):253–257. doi:10.1016/j.buildenv.2006.02.025
- Yao KS, Wang DY, Chang CY, Weng KW, Yang LY, Lee SJ, Cheng TC, Hwang CC (2007a) Photocatalytic disinfection of phyto-pathogenic bacteria by dye-sensitized TiO<sub>2</sub> thin film activated by visible light. Surf Coat Technol 202(4–7):1329–1332. doi:10.1016/j.surfcoat.2007.07.102
- Yao KS, Wang DY, Ho WY, Yan JJ, Tzeng KC (2007b) Photocatalytic bactericidal effect of TiO<sub>2</sub> thin film on plant pathogens. Surf Coat Technol 201(15):6886–6888. doi:10.1016/j.surfcoat.2006.09.068
- Yao KS, Wang DY, Yan JJ, Yang LY, Chen WS (2007c) Photocatalytic effects of TiO<sub>2</sub>/Fe thin film irradiated with visible light on cellular surface ultrastructure and genomic DNA of bacteria. Surf Coat Technol 201(15):6882–6885. doi:10.1016/j.surfcoat.2006.09.066
- Yao KS, Cheng TC, Li SJ, Yang LY, Tzeng KC, Chang CY, Ko Y (2008a) Comparison of photocatalytic activities of various dye-modified TiO<sub>2</sub> thin films under visible light. Surf Coat Technol 203(5–7):922–924
- Yao KS, Wang DY, Chang CY, Ho WY, Yang LY (2008b) Characteristics and photocatalytic activity of TiO<sub>2</sub> thin film sensitized with a porphyrin dye. J Nanosci Nanotechnol 8(5):2699–2702. doi:10.1166/jnn.2008.495
- Yao Y, Ohko Y, Sekiguchi Y, Fujishima A, Kubota Y (2008c) Self-sterilization using silicone catheters coated with Ag and TiO<sub>2</sub> nanocomposite thin film. J Biomed Mater Res B 85B(2):453–460. doi:10.1002/jbm.b.30965
- Yates HM, Brook LA, Ditta IB, Evans P, Foster HA, Sheel DW, Steele A (2008a) Photo-induced self-cleaning and biocidal behaviour of titania and copper oxide multilayers. J Photochem Photobiol A 195(2–3):197–205
- Yates HM, Brook LA, Sheel DW, Ditta IB, Steele A, Foster HA (2008b) The growth of copper oxides on glass by flame assisted chemical vapour deposition. Thin Solid Films 517(2):517–521
- Yu JC, Tang HY, Yu JG, Chan HC, Zhang LZ, Xie YD, Wang H, Wong SP (2002) Bactericidal and photocatalytic activities of TiO<sub>2</sub> thin films prepared by sol-gel and reverse micelle methods. J Photochem Photobiol A 153(1–3):211–219
- Yu JC, Ho WK, Lin J, Yip KY, Wong PK (2003a) Photocatalytic activity, antibacterial effect, and photoinduced hydrophilicity of TiO<sub>2</sub> films coated on a stainless steel substrate. Environ Sci Technol 37(10):2296–2301. doi:10.1021/es0259483
- Yu JC, Xie Y, Tang HY, Zhang L, Chan HC, Zhao J (2003b) Visible light-assisted bactericidal effect of metalphthalocyanine-sensitized titanium dioxide films. J Photochem Photobiol A 156(1–3):235–241
- Yu J, Xiong J, Cheng B, Liu S (2005a) Fabrication and characterization of Ag-TiO<sub>2</sub> multiphase nanocomposite thin films with enhanced photocatalytic activity. Appl Catal B 60(3–4):211–221
- Yu JC, Ho W, Yu J, Yip H, Po KW, Zhao J (2005b) Efficient visible-light-induced photocatalytic disinfection on sulfur-doped nanocrystalline titania. Environ Sci Technol 39(4):1175–1179
- Yu KP, Lee GWM, Lin ZY, Huang CP (2008) Removal of bioaerosols by the combination of a photocatalytic filter and negative air ions. J Aerosol Sci 39(5):377–392. doi:10.1016/j.jaerosci.2007.12.005
- Yuranova T, Rincon AG, Pulgarin C, Laub D, Xantopoulos N, Mathieu HJ, Kiwi J (2006) Performance and characterization of Ag-cotton and Ag/TiO<sub>2</sub> loaded textiles during the abatement of *E. coli*. J Photochem Photobiol A 181(2–3):363–369. doi:10.1016/j.jphotochem.2005.12.020
- Zan L, Fa W, Peng T, Gong ZK (2007) Photocatalysis effect of nanometer TiO<sub>2</sub> and TiO<sub>2</sub>-coated ceramic plate on hepatitis B virus. J Photochem Photobiol B 86(2):165–169. doi:10.1016/j.jphotobiol.2006.09.002